



Precision Crystal Calorimeters in High Energy Physics: Past, Present and Future

Ren-Yuan Zhu

California Institute of Technology





Physics with Crystal Calorimeters



Charmonium system observed by CB through Inclusive photons

$H \rightarrow \gamma\gamma$ at LHC

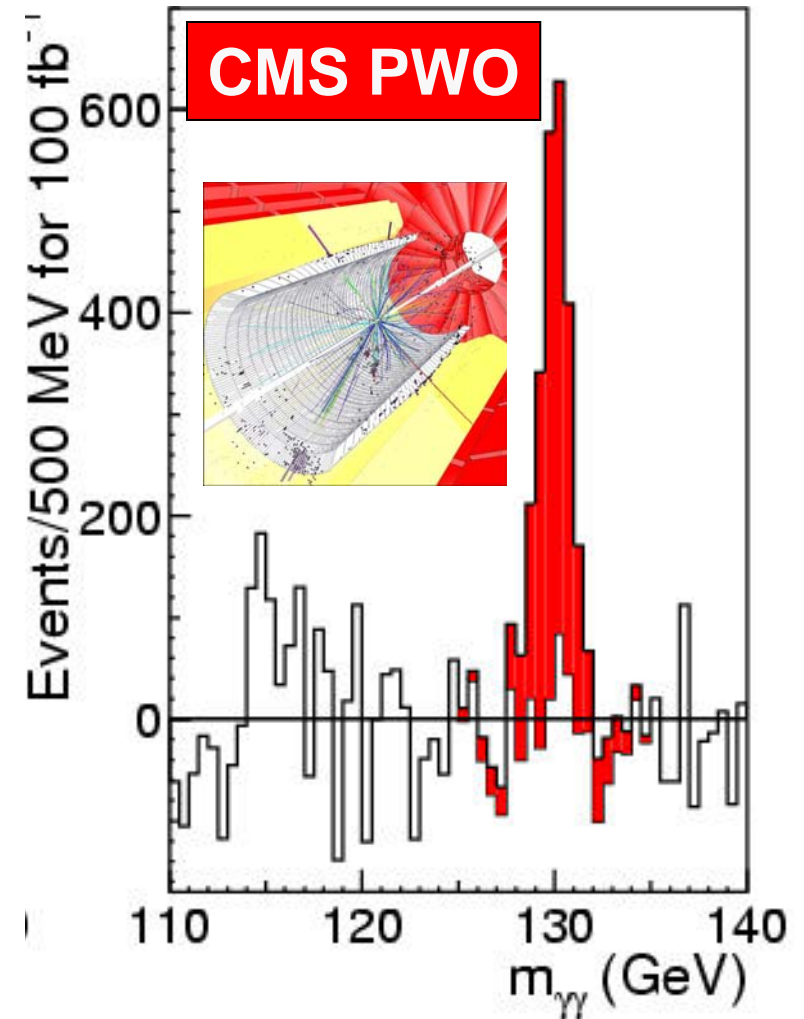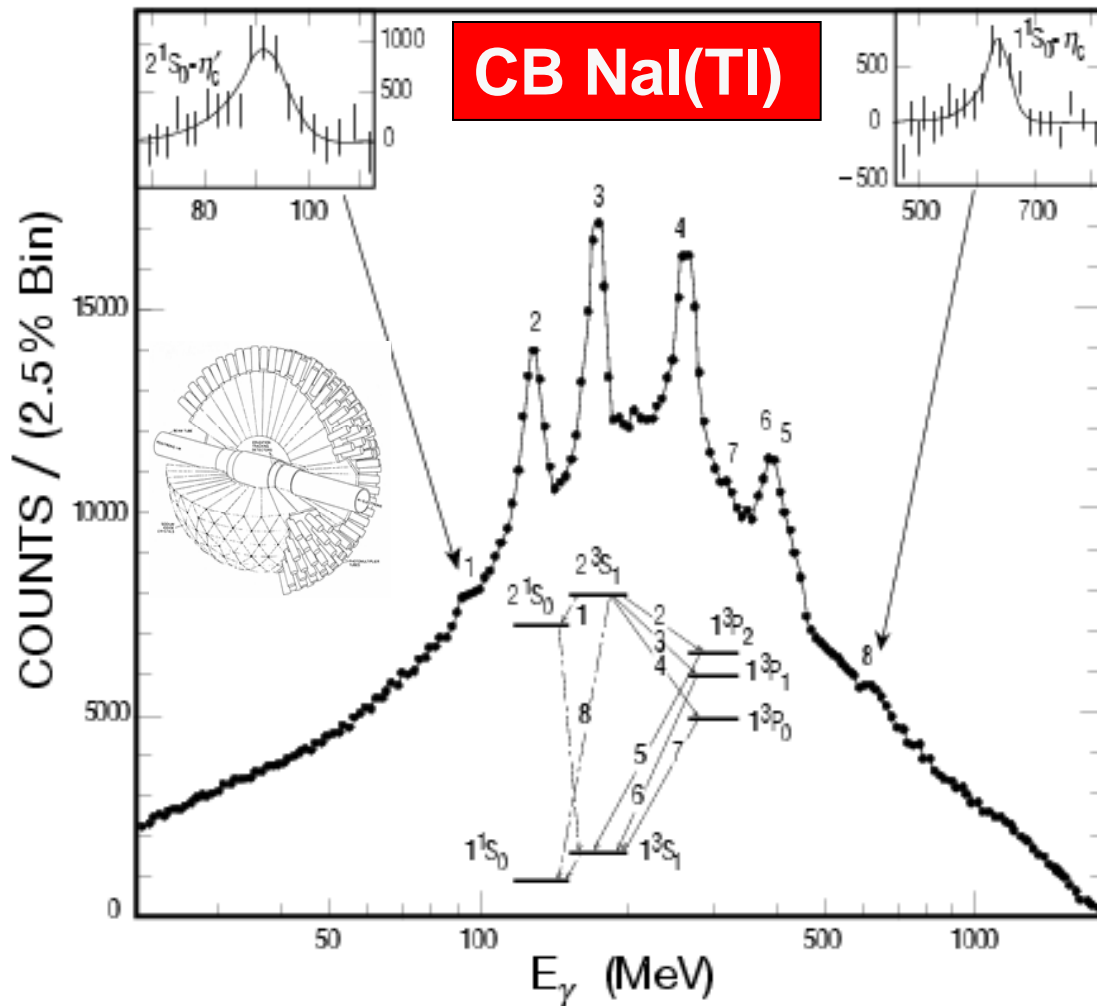



Mass Produced Crystals




Crystal	Nal(Tl)	CsI(Tl)	CsI	BaF ₂	BGO	PWO(Y)	LSO(Ce)	GSO(Ce)
Density (g/cm ³)	3.67	4.51	4.51	4.89	7.13	8.3	7.40	6.71
Melting Point (°C)	651	621	621	1280	1050	1123	2050	1950
Radiation Length (cm)	2.59	1.86	1.86	2.03	1.12	0.89	1.14	1.38
Molière Radius (cm)	4.13	3.57	3.57	3.10	2.23	2.00	2.07	2.23
Interaction Length (cm)	42.9	39.3	39.3	30.7	22.8	20.7	20.9	22.2
Refractive Index ^a	1.85	1.79	1.95	1.50	2.15	2.20	1.82	1.85
Hygroscopicity	Yes	Slight	Slight	No	No	No	No	No
Luminescence ^b (nm) (at peak)	410	550	420 310	300 220	480	425 420	402	440
Decay Time ^b (ns)	230	1250	30 6	630 0.9	300	30 6	40	60
Light Yield ^{b,c} (%)	100	165	3.6 1.1	36 3.4	21	0.29 .083	83	30
d(LY)/dT ^b (%/°C)	~0	0.3	-0.6	-2 ~0	-1.6	-1.9	~0	-0.1
Experiment	Crystal Ball	CLEO BaBar BELLE BES III	KTeV	TAPS (L*) (GEM)	L3 BELLE PANDA?	CMS ALICE PrimEx PANDA?	-	-


a. at peak of emission; b. up/low row: slow/fast component; c. PMT QE taken out.



Crystal Density: Radiation Length

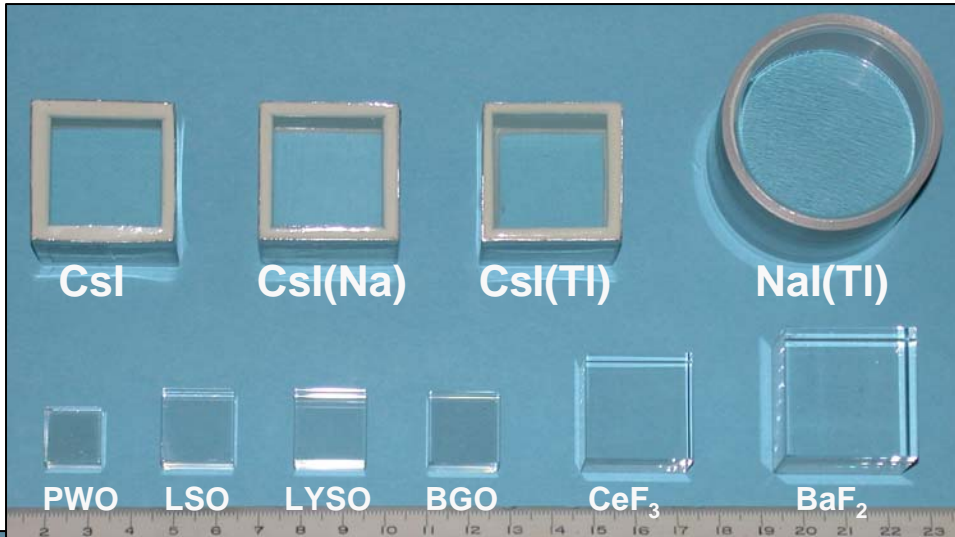

1.5 X_0 Samples:
Hygroscopic Halides
Non-hygroscopic

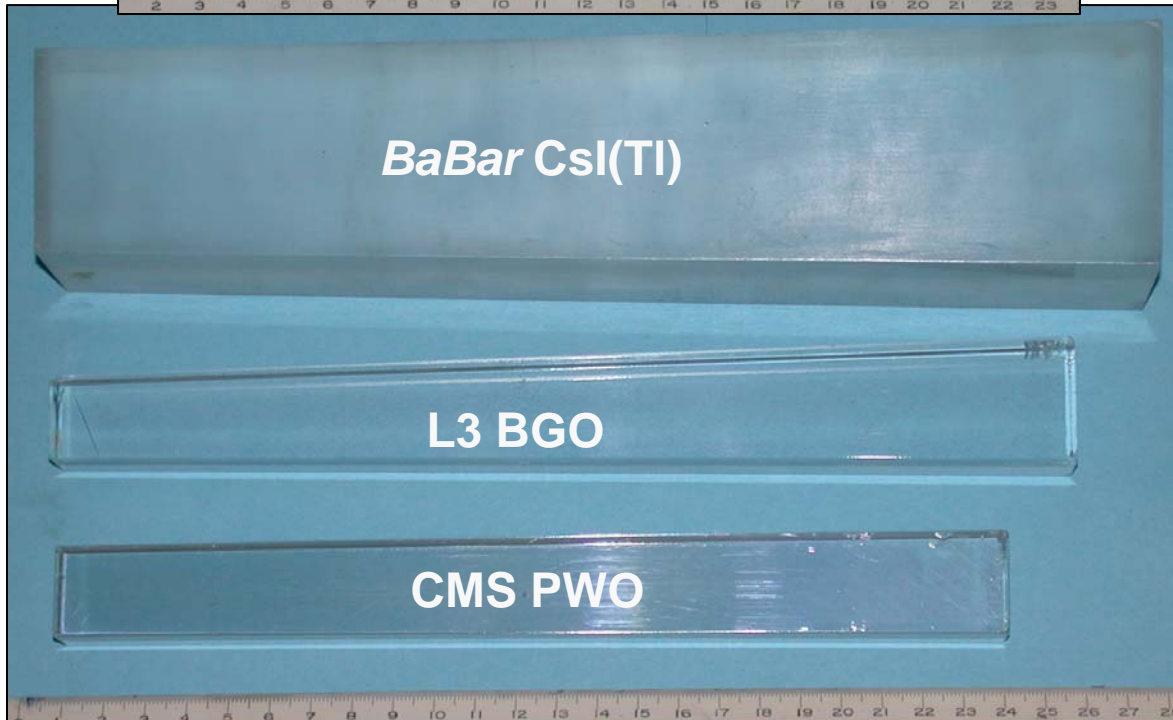

Full Size Crystals:
BaBar Csl(Tl): 16 X_0
L3 BGO: 22 X_0
CMS PWO(Y): 25 X_0




Excitation, Emission & Transmission



$T_s = (1 - R)^2 + R^2(1 - R)^2 + \dots = (1 - R)/(1 + R)$, with

$$R = \frac{(n_{crystal} - n_{air})^2}{(n_{crystal} + n_{air})^2}$$

Theoretical limit of transmittance: NIM A333 (1993) 422

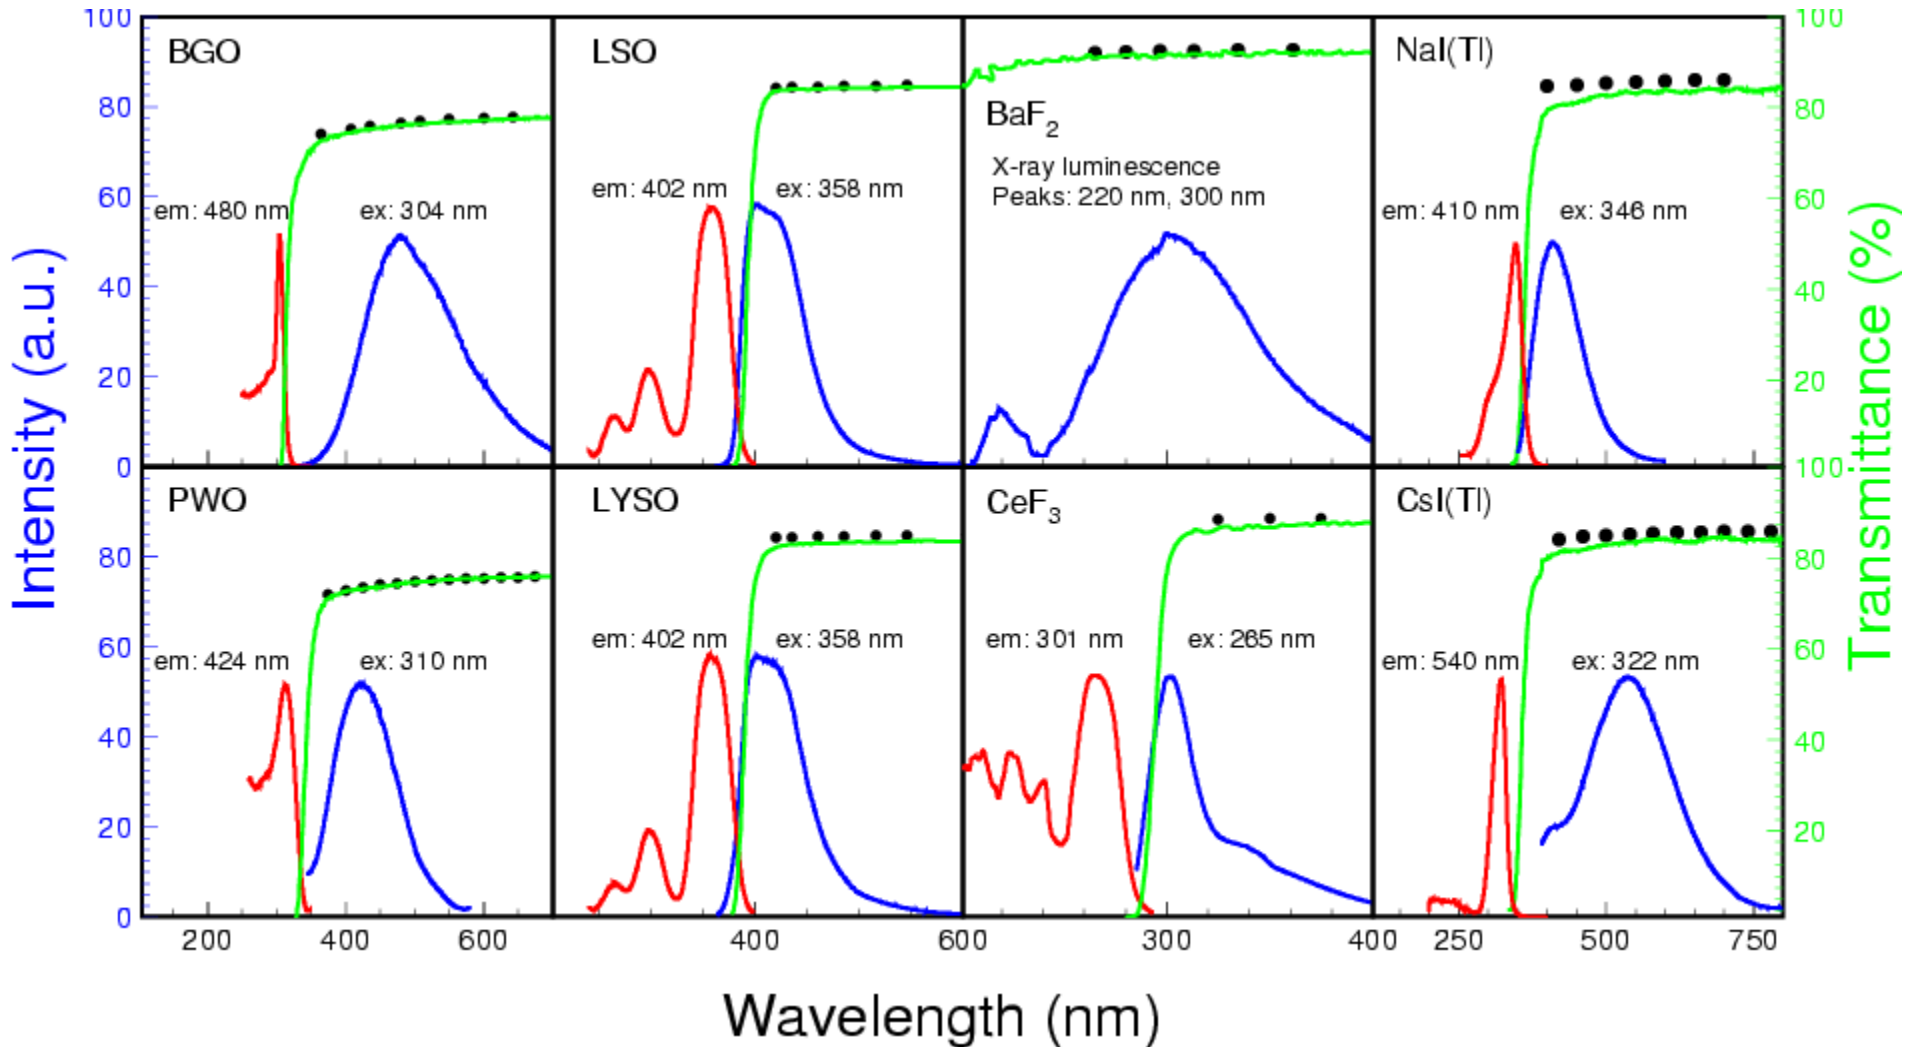




Scintillation Light Decay Time




Recorded with an Agilent 6052A digital scope

Fast Scintillators

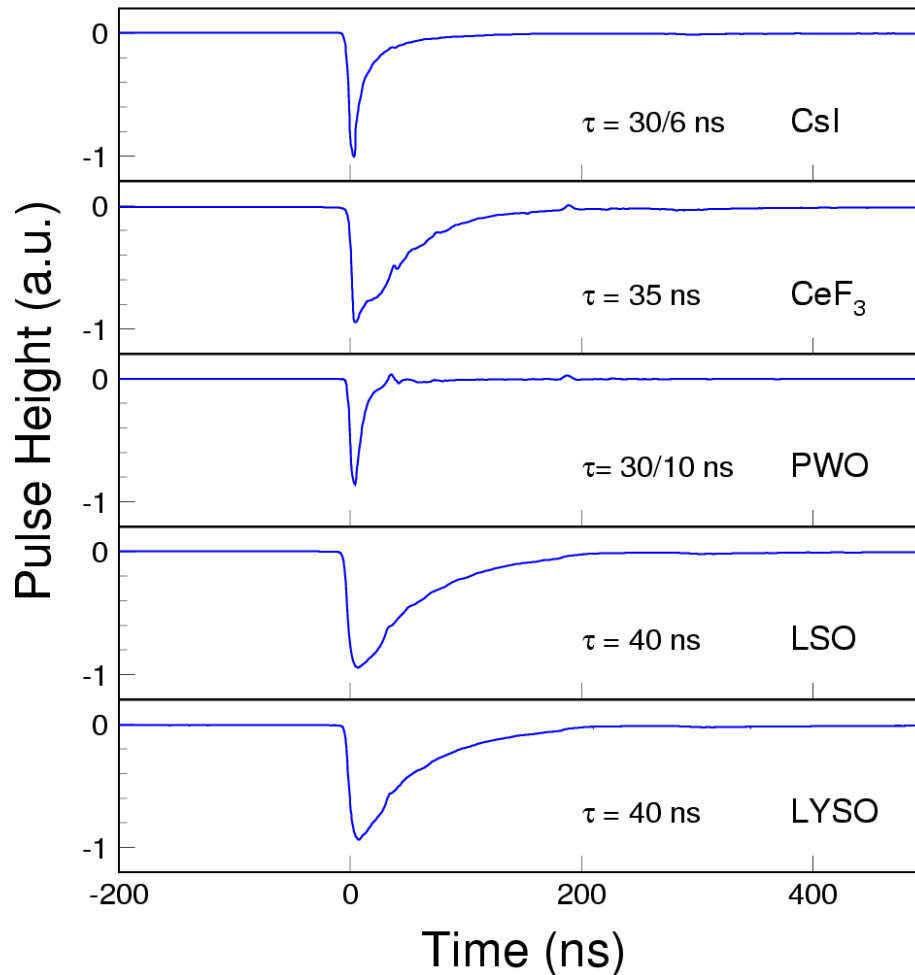

Slow Scintillators

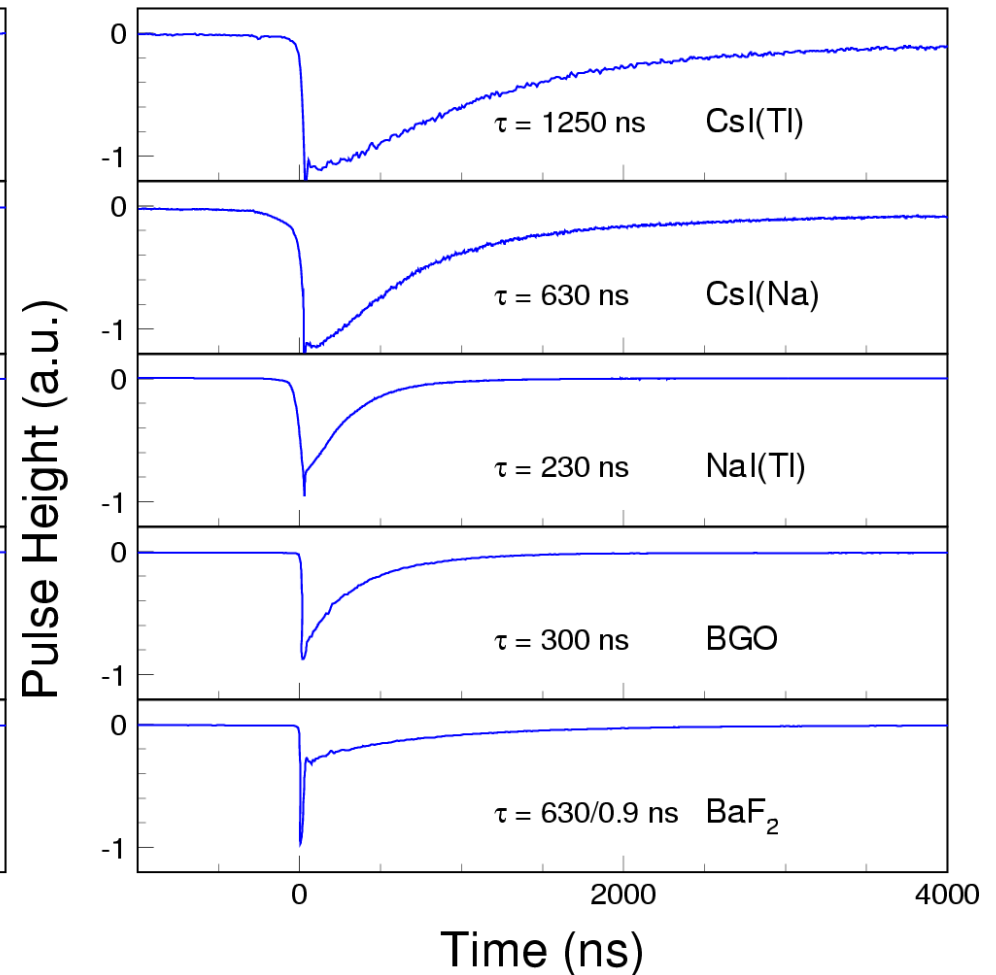




Scintillation Light Output




Measured with a Philips XP2254B PMT (multi-alkali cathode)
 p.e./MeV: LSO/LYSO is 6 & 230 times of BGO & PWO respectively

Fast Scintillators

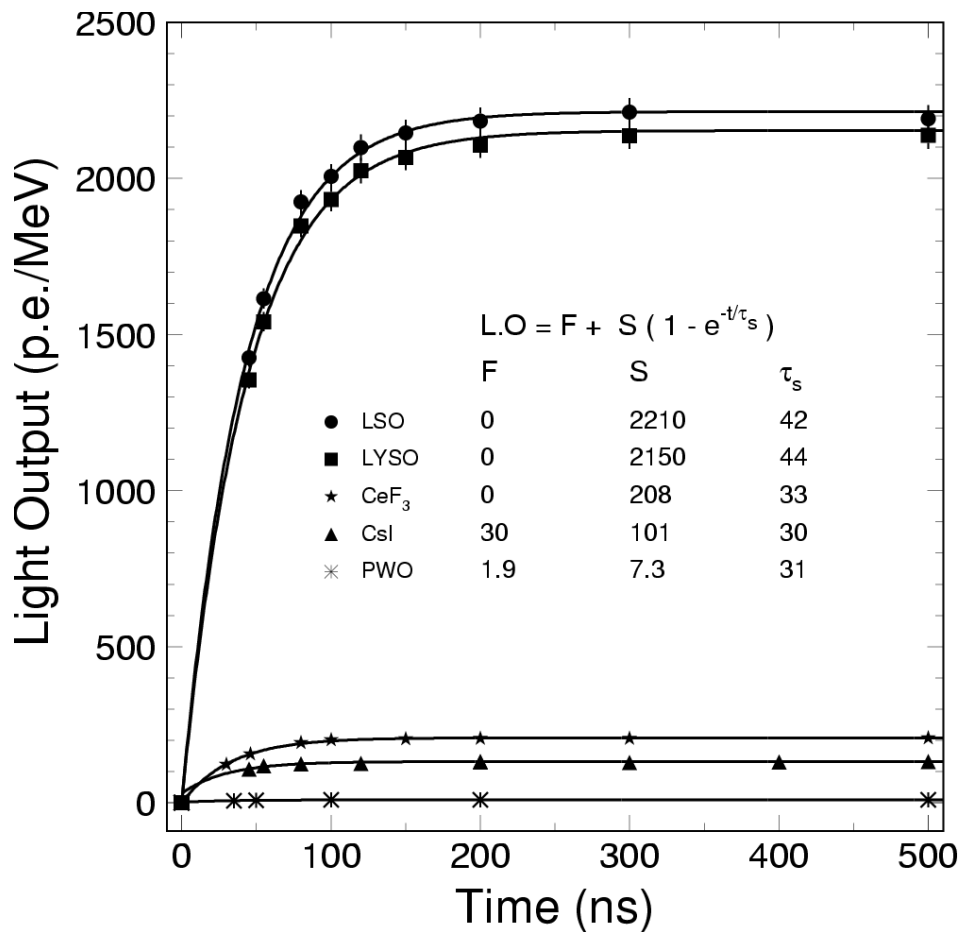

Slow Scintillators


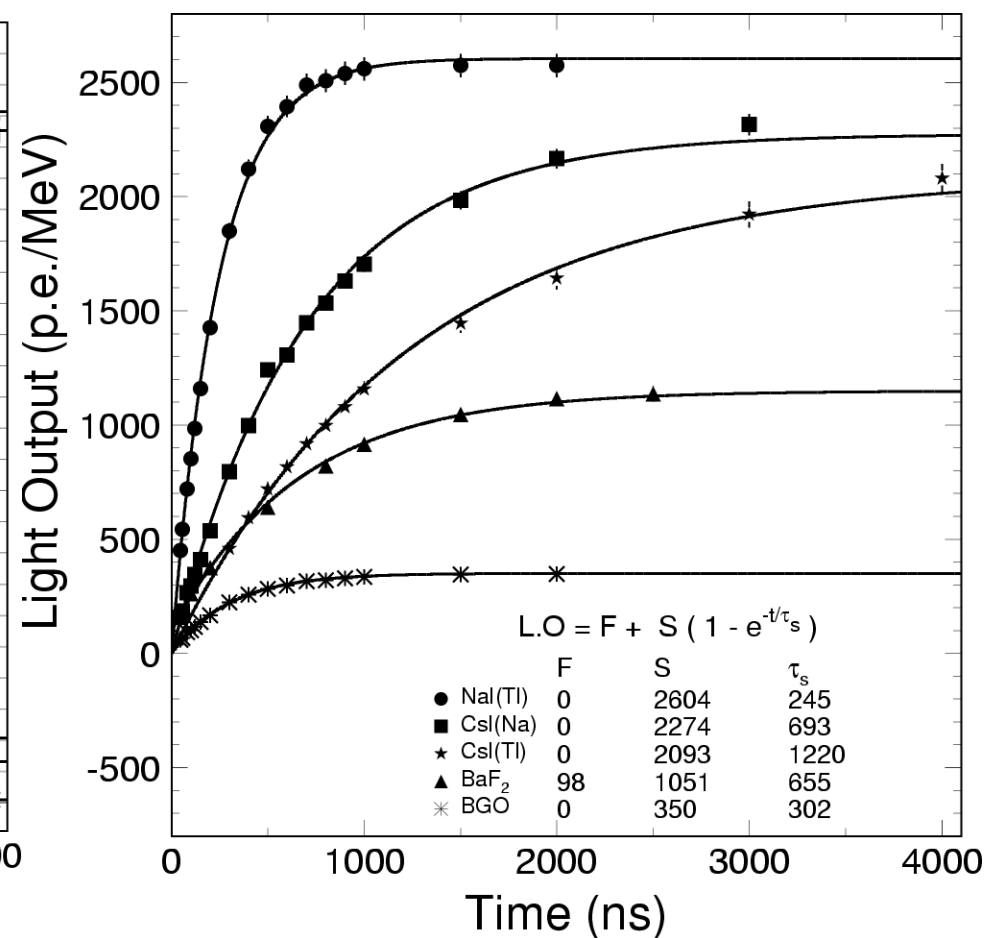




Emission weighted PMT Q.E.



Taking out QE, L.O. of LSO/LYSO is 4/220 times BGO/PWO
Hamamatsu S8664-55 APD has QE 75% for LSO/LYSO

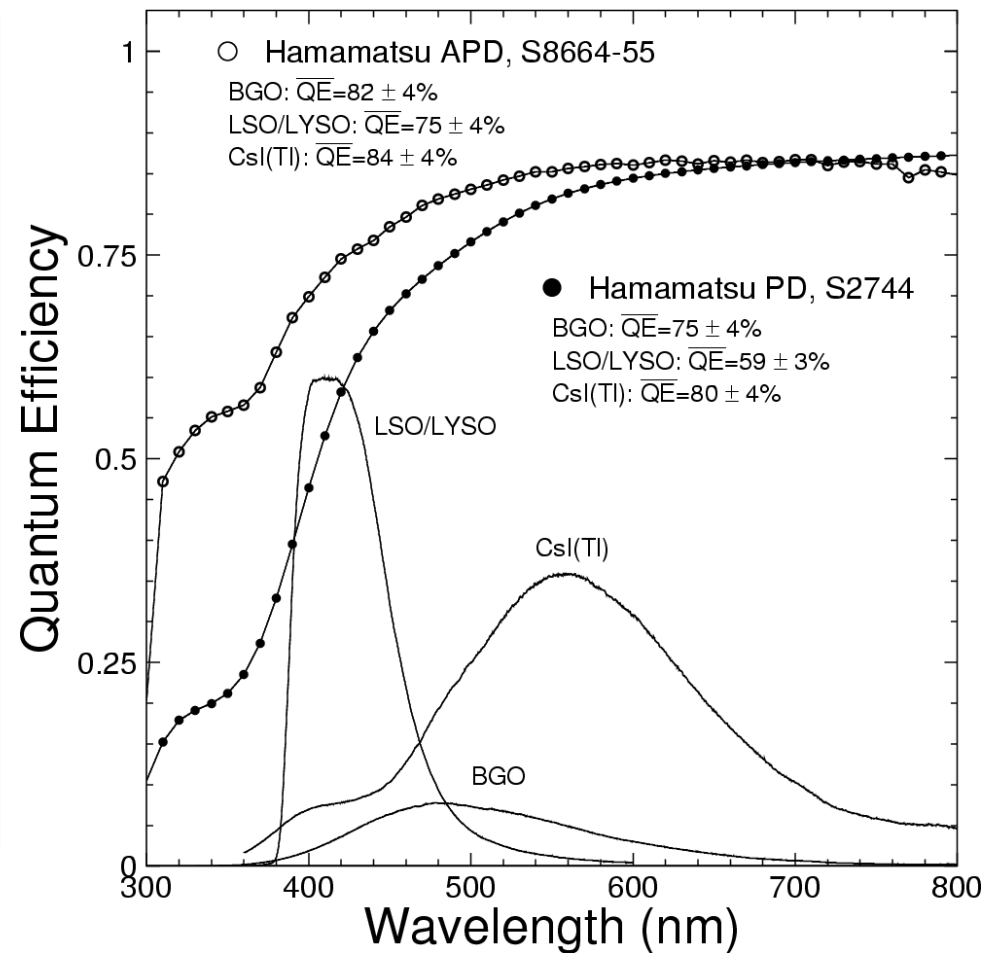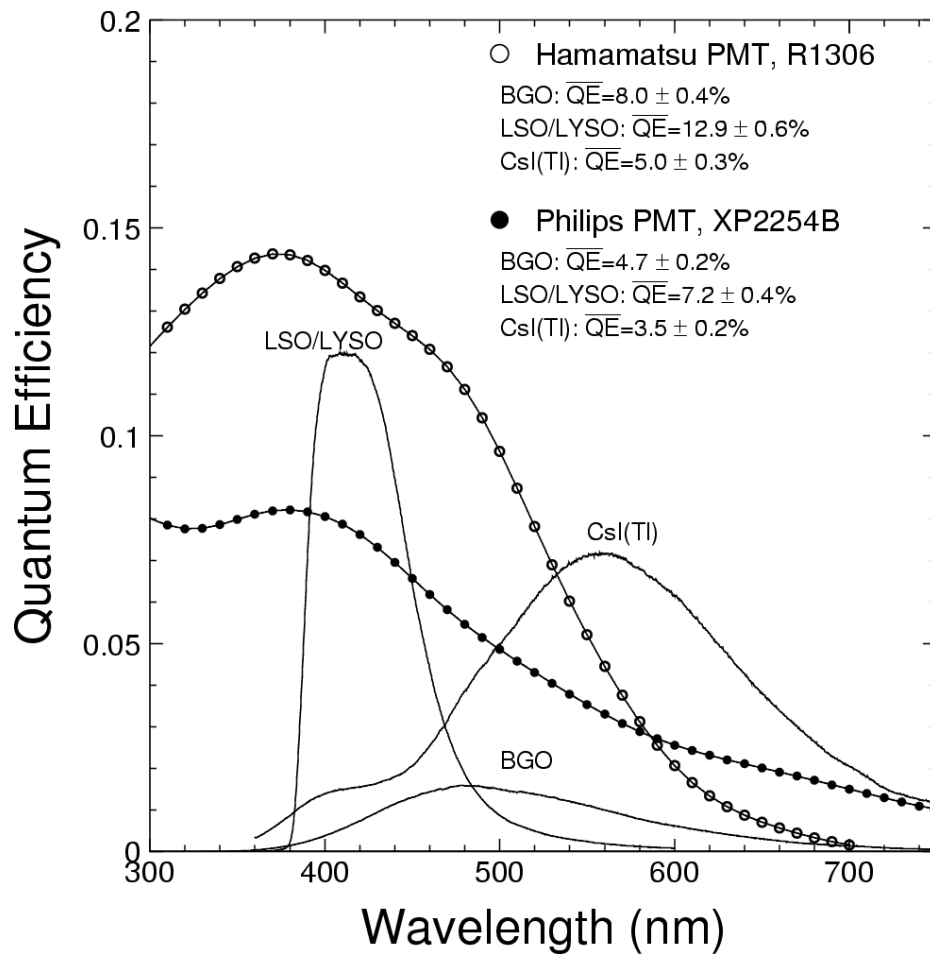




BGO, LSO & LYSO Samples



2.5 x 2.5 x 20 cm (18 X₀)


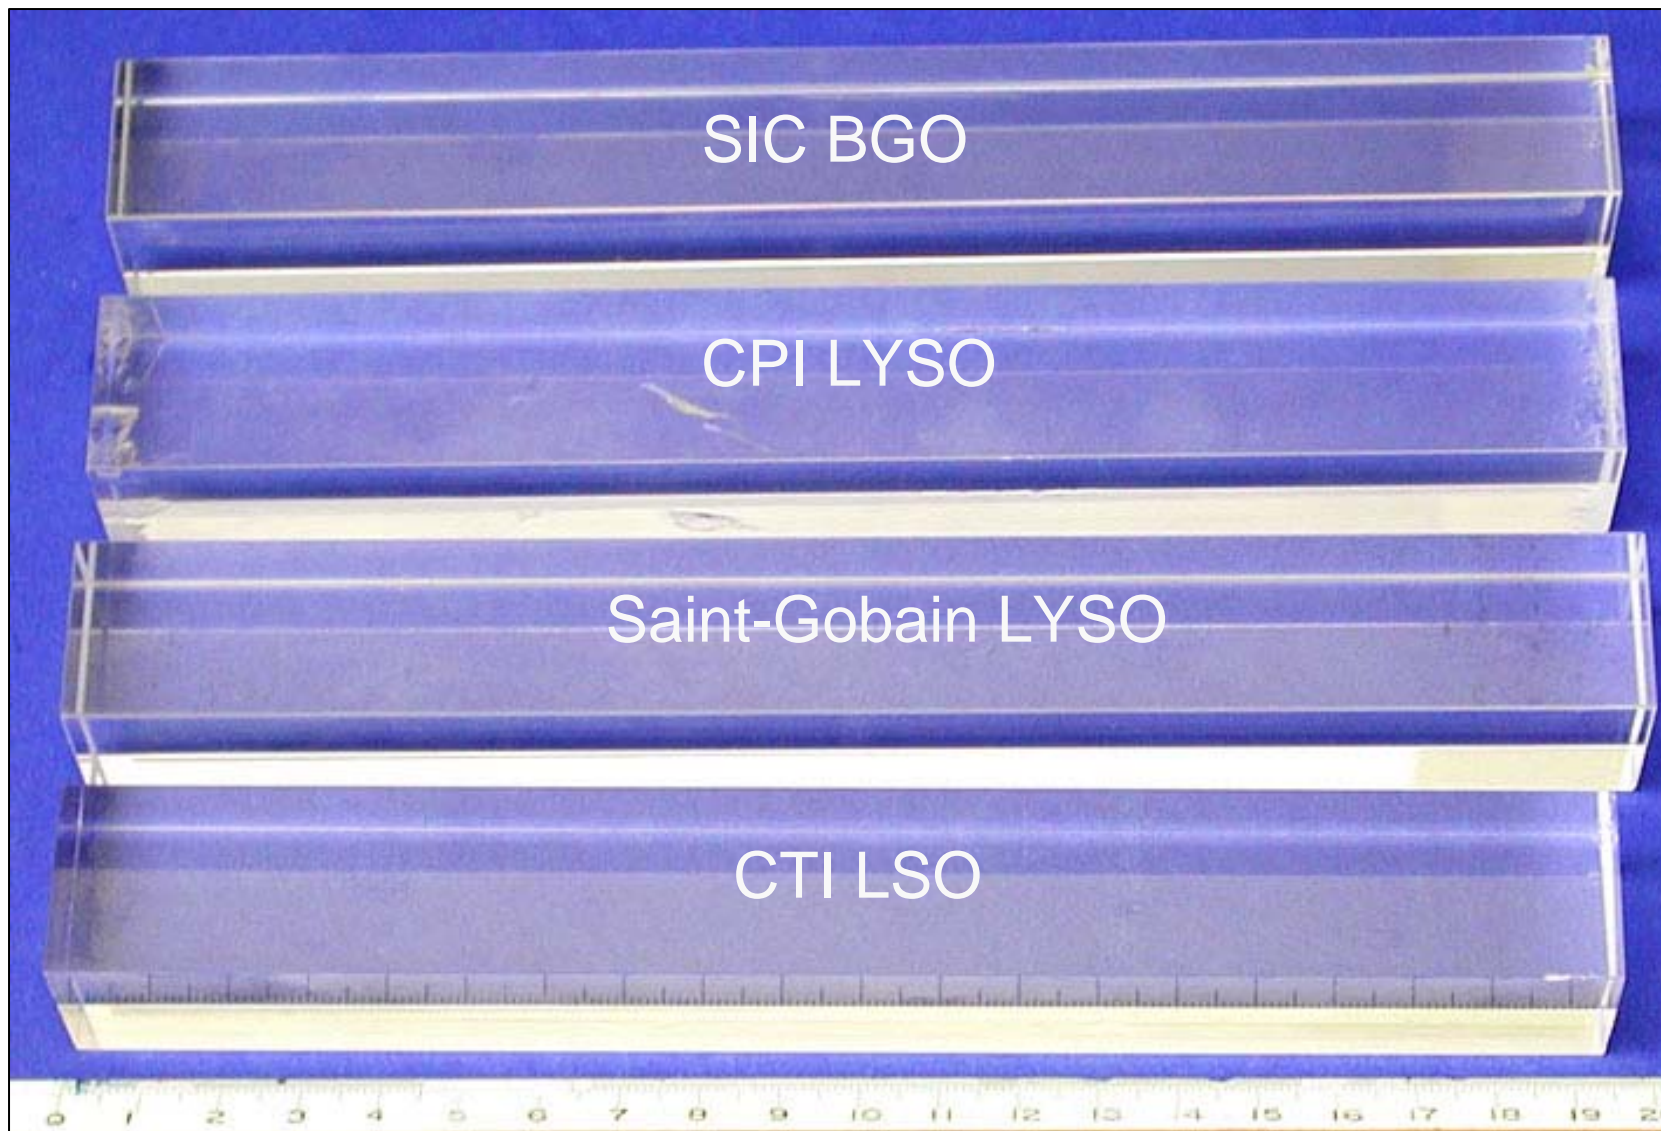




LSO/LYSO with PMT Readout



~10% FWHM resolution for ^{22}Na source (0.51 MeV)
1,200 p.e./MeV, 5/230 times of BGO/PWO

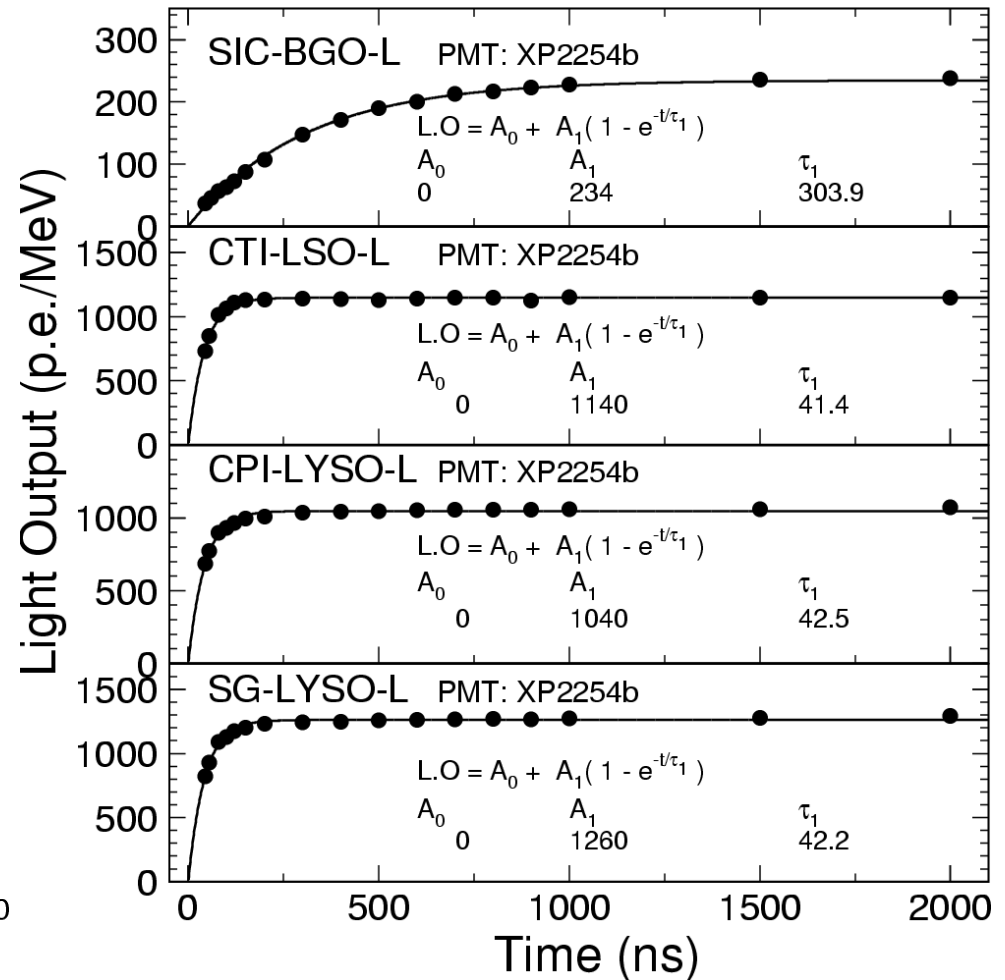
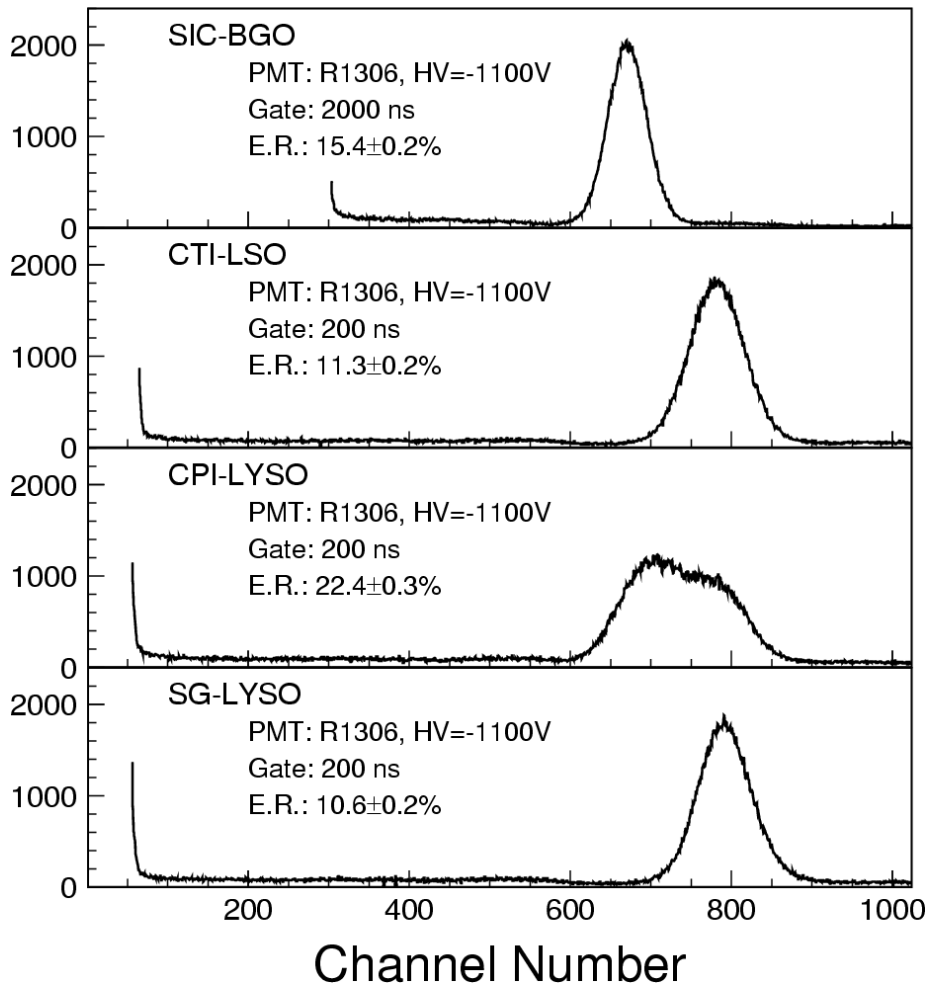




LSO/LYSO with APD Readout



L.O.: 1,500 p.e./MeV, 4/200 times of BGO/PWO
Readout Noise: <40 keV

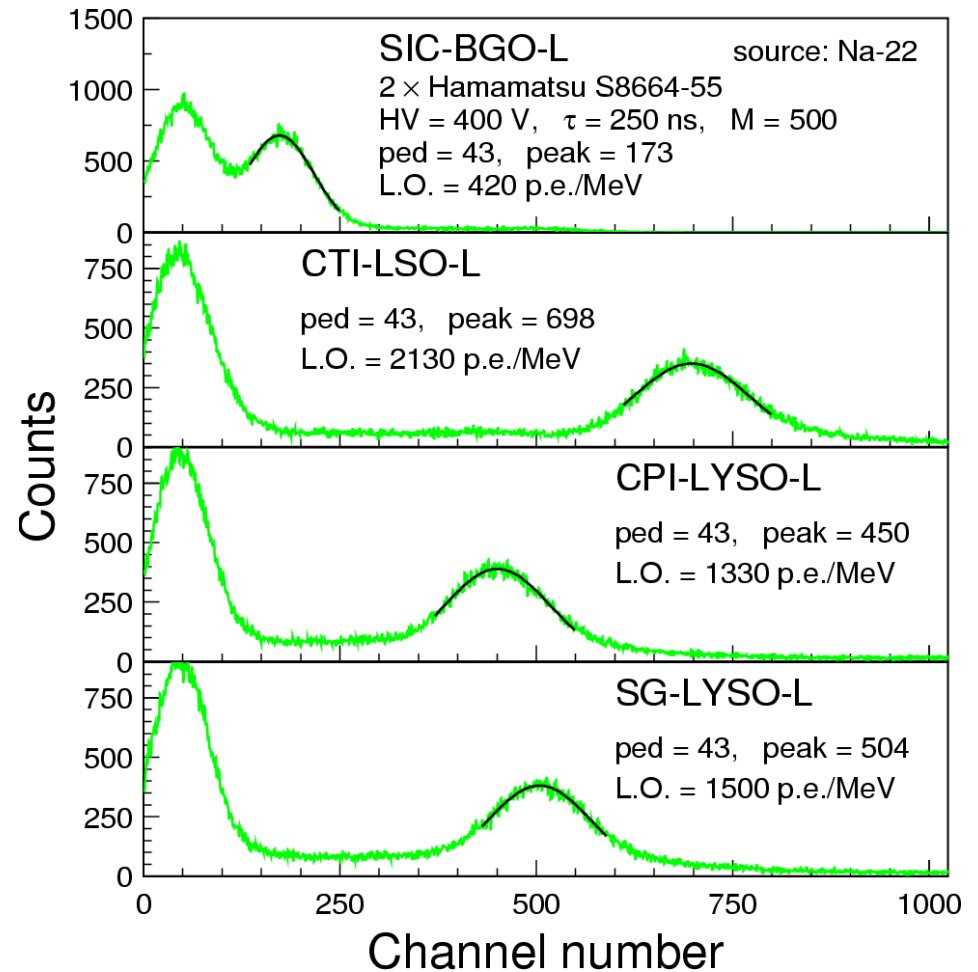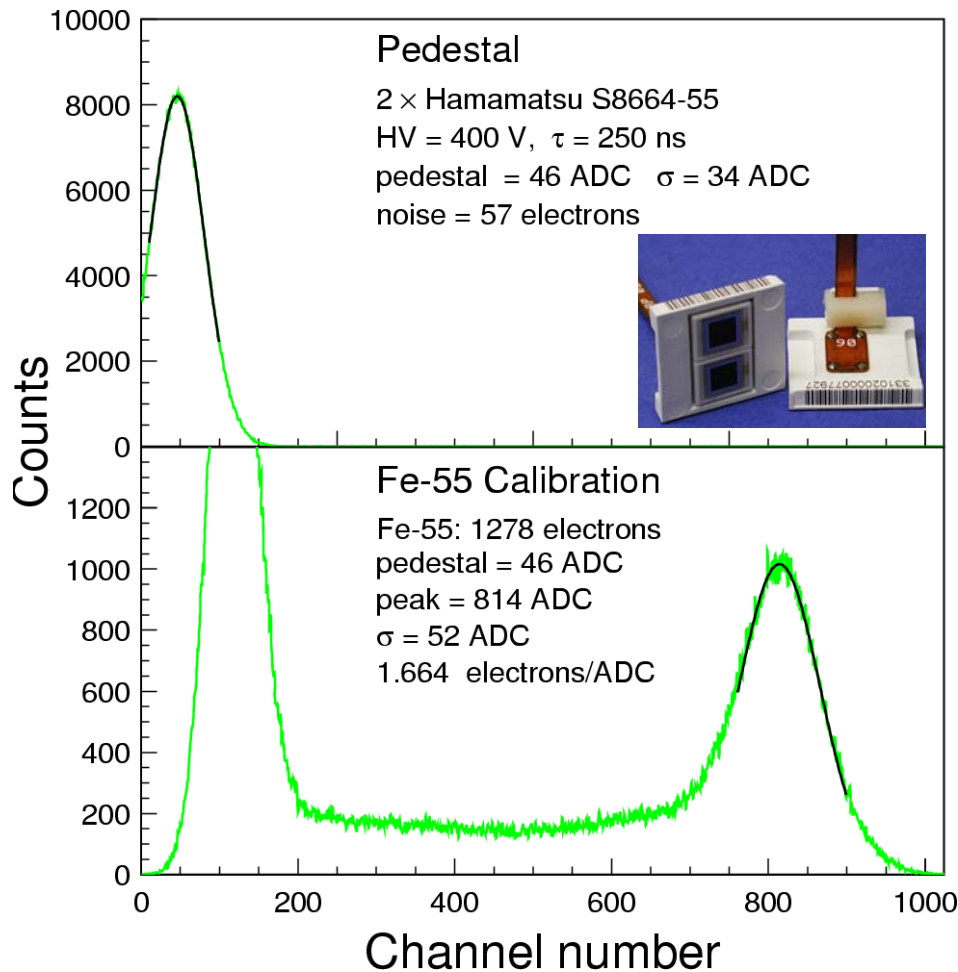



Crystal Calorimeters in HEP



Date	75-85	80-00	80-00	80-00	90-10	94-10	94-10	95-20
Experiment	C. Ball	L3	CLEO II	C. Barrel	KTeV	<i>BaBar</i>	BELLE	CMS
Accelerator	SPEAR	LEP	CESR	LEAR	FNAL	SLAC	KEK	CERN
Crystal Type	NaI(Tl)	BGO	CsI(Tl)	CsI(Tl)	CsI	CsI(Tl)	CsI(Tl)	PbWO ₄
B-Field (T)	-	0.5	1.5	1.5	-	1.5	1.0	4.0
r_{inner} (m)	0.254	0.55	1.0	0.27	-	1.0	1.25	1.29
Number of Crystals	672	11,400	7,800	1,400	3,300	6,580	8,800	76,000
Crystal Depth (X_0)	16	22	16	16	27	16 to 17.5	16.2	25
Crystal Volume (m ³)	1	1.5	7	1	2	5.9	9.5	11
Light Output (p.e./MeV)	350	1,400	5,000	2,000	40	5,000	5,000	2
Photosensor	PMT	Si PD	Si PD	WS ^a +Si PD	PMT	Si PD	Si PD	APD ^a
Gain of Photosensor	Large	1	1	1	4,000	1	1	50
σ_N /Channel (MeV)	0.05	0.8	0.5	0.2	small	0.15	0.2	40
Dynamic Range	10 ⁴	10 ⁵	10 ⁴	10 ⁴	10 ⁴	10 ⁴	10 ⁴	10 ⁵



Future crystal calorimeters in HEP:
PANDA at GSI: PWO or BGO?
LSO/LYSO for a Super B Factory or ILC?



L3 BGO Resolution





Contribution	“Radiative”+Intrinsic	Temperature	Calibration	Overall
Barrel	0.8%	0.5%	0.5%	1.07%
Endcaps	0.6%	0.5%	0.4%	0.88%

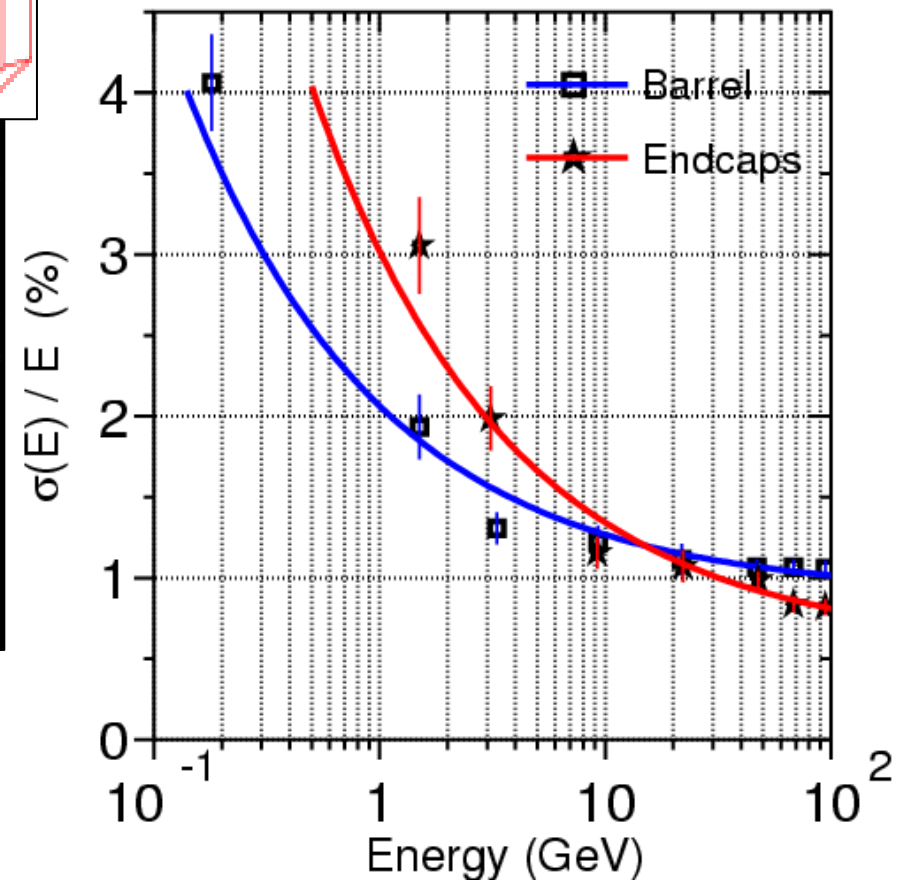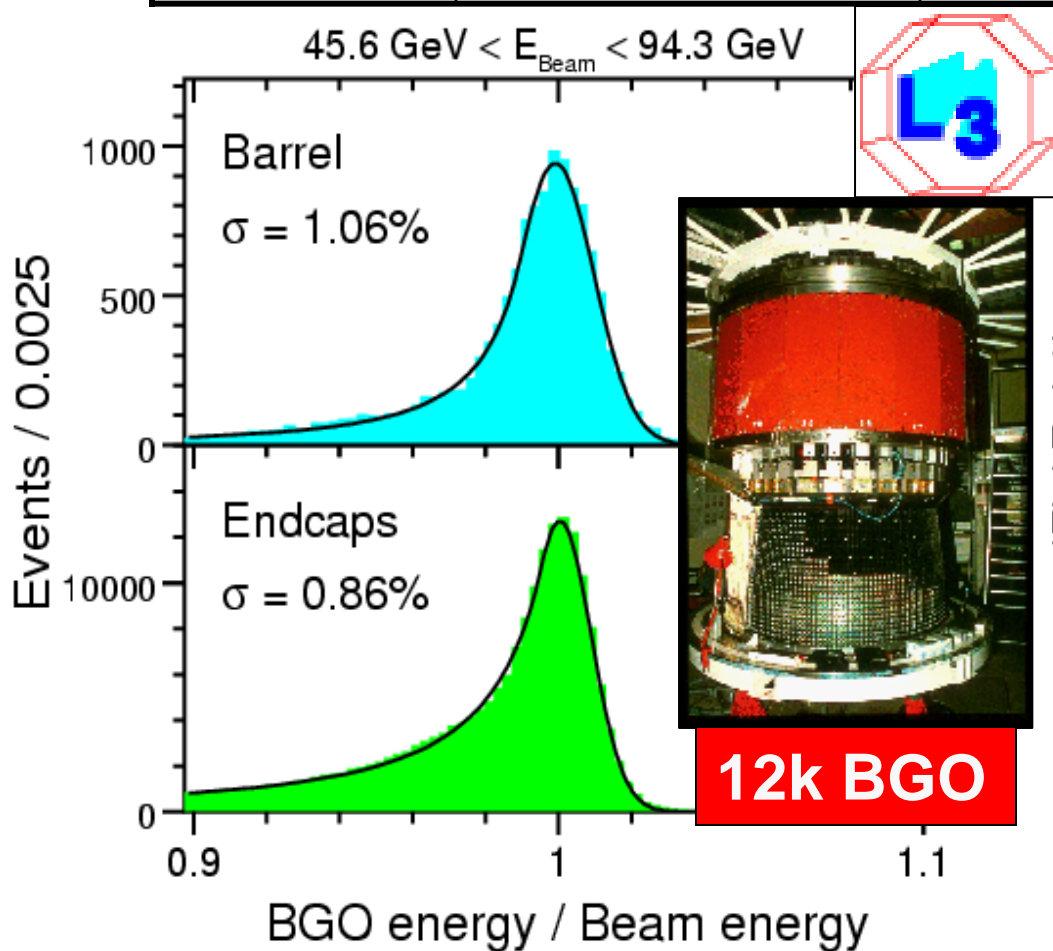






KTeV CsI Position Resolution

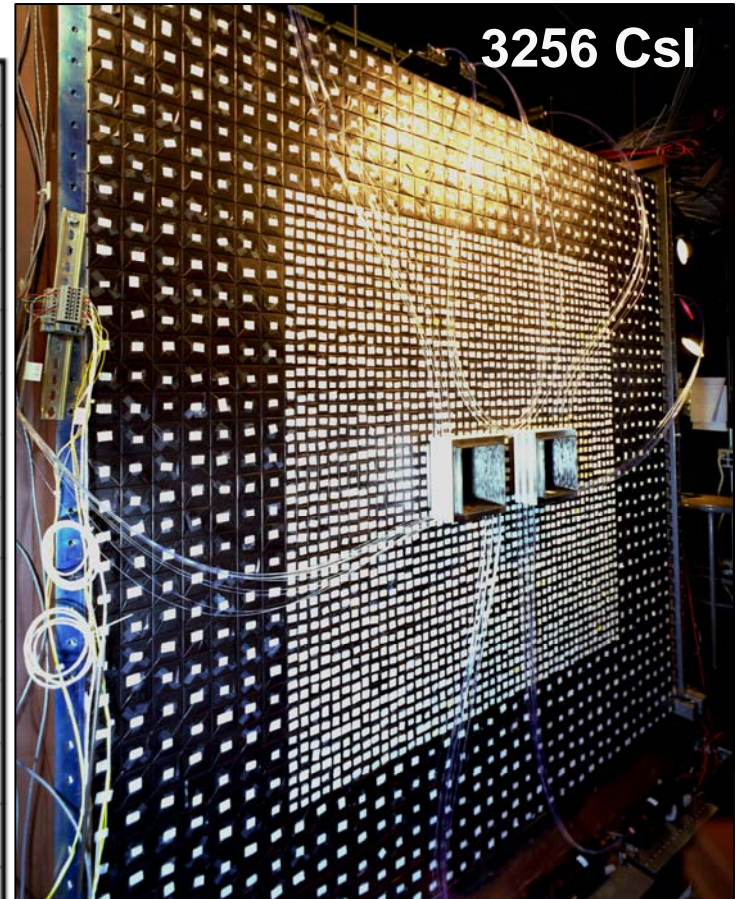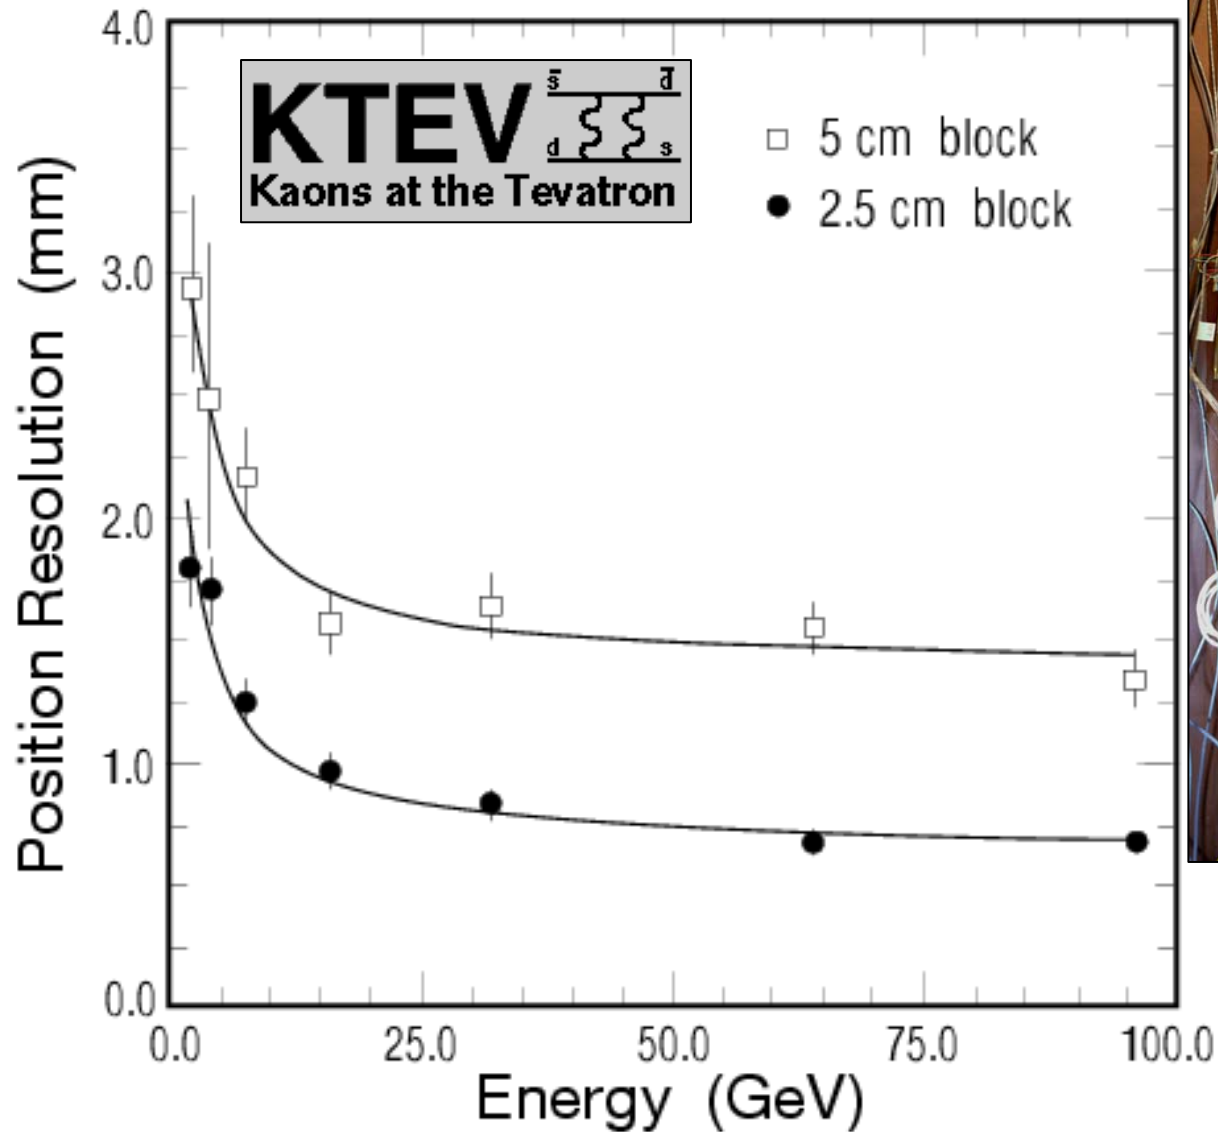

Sub mm position resolution.
L3 BGO & CMS
PWO: 0.3 mm.



BaBar CsI(Tl) Resolution

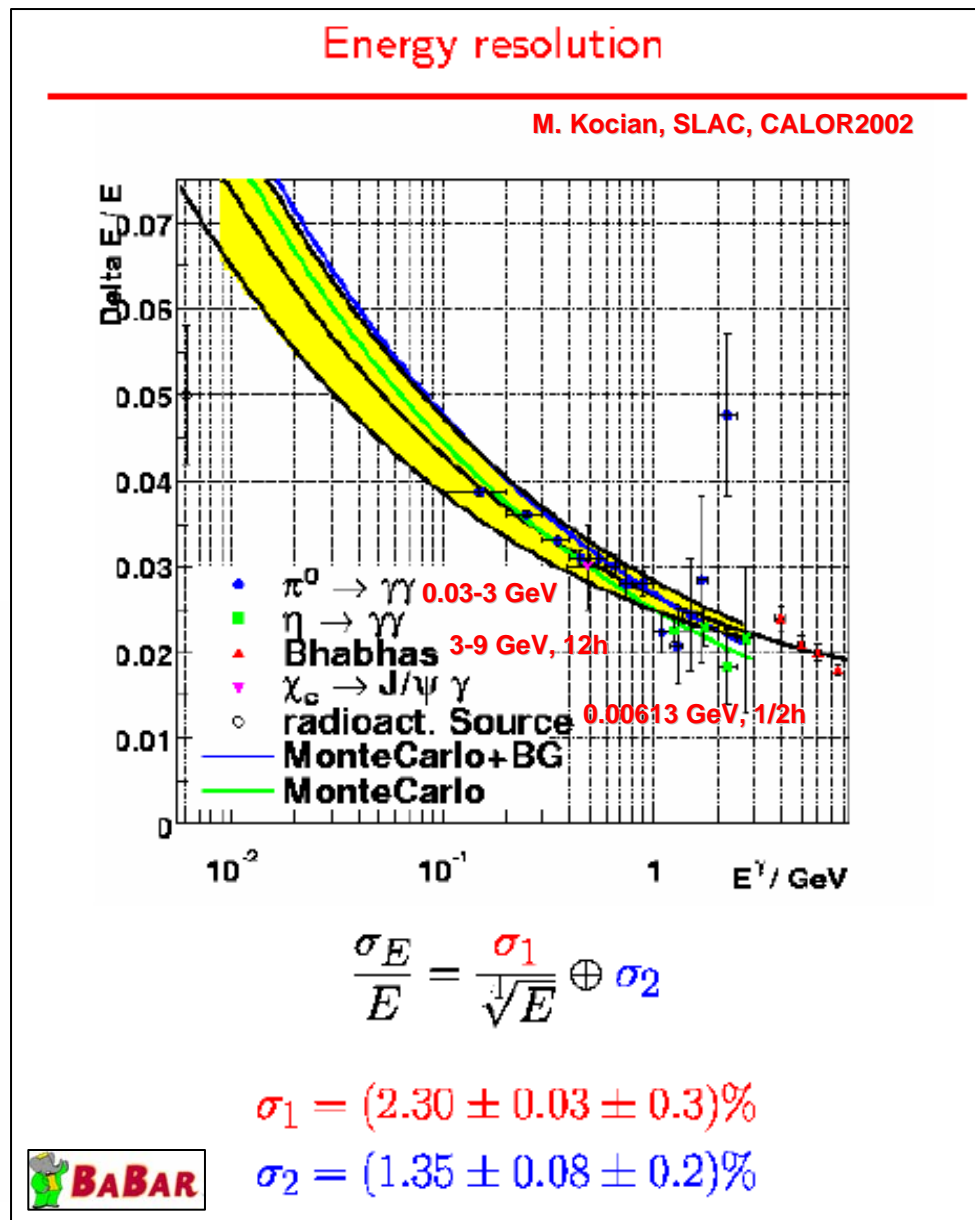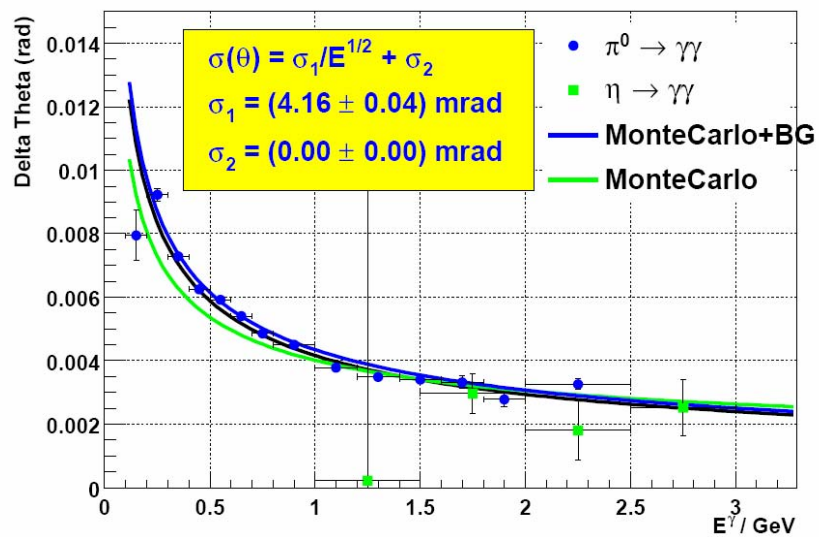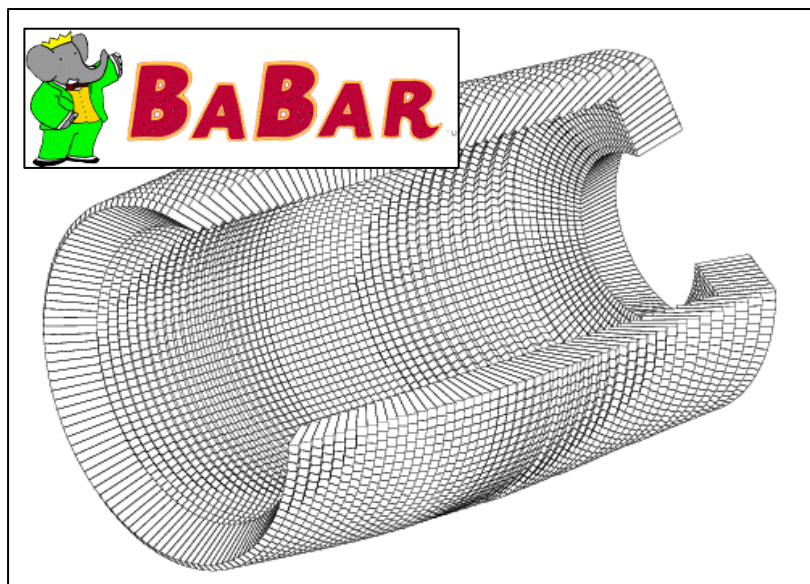




PWO Crystal ECAL Resolution



Crystal Aging & Radiation Damage?


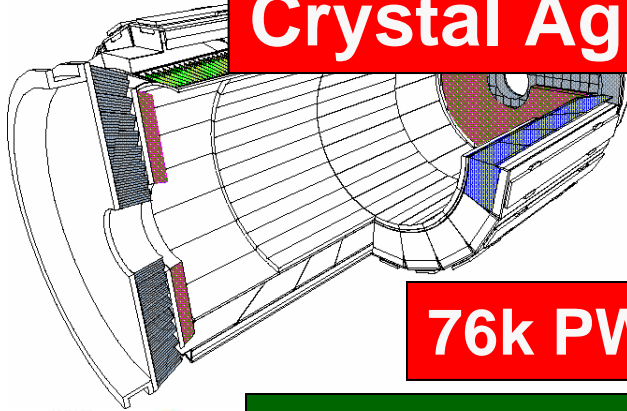


76k PWO



Measured Resolution
 $\sigma(E)/E < 1\%$ if $E > 25$ GeV
 $\sigma(E)/E \sim 0.5\%$ at 120 GeV

Designed Resolution

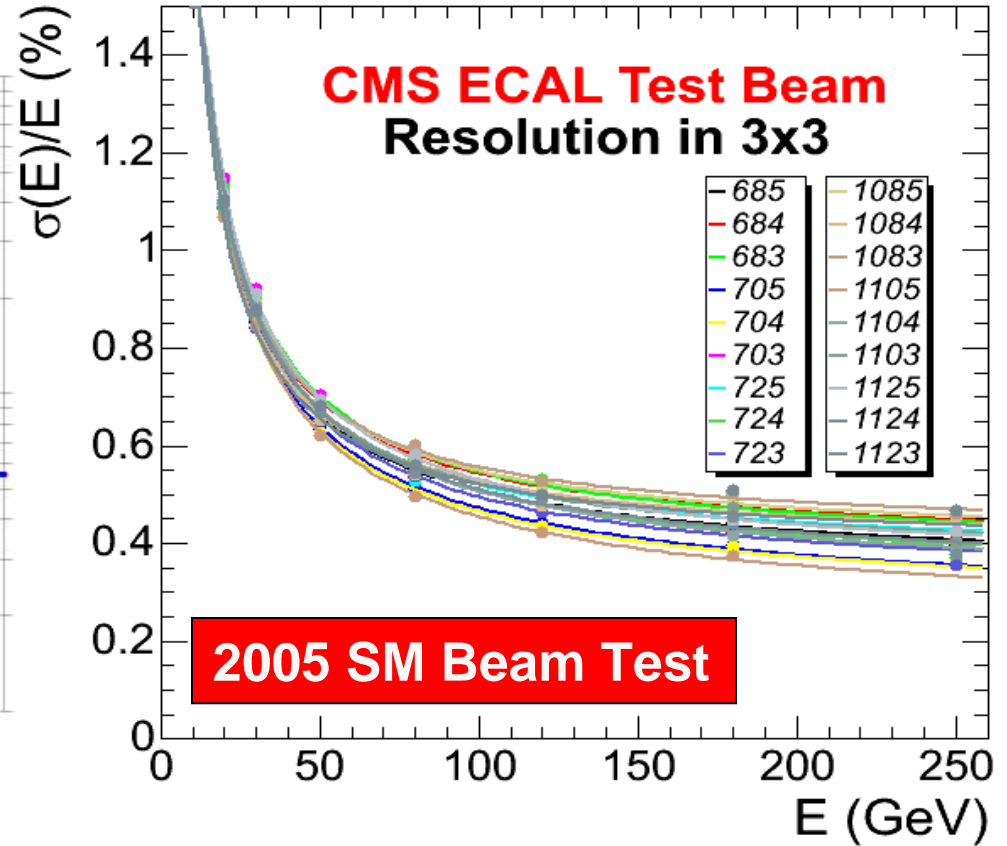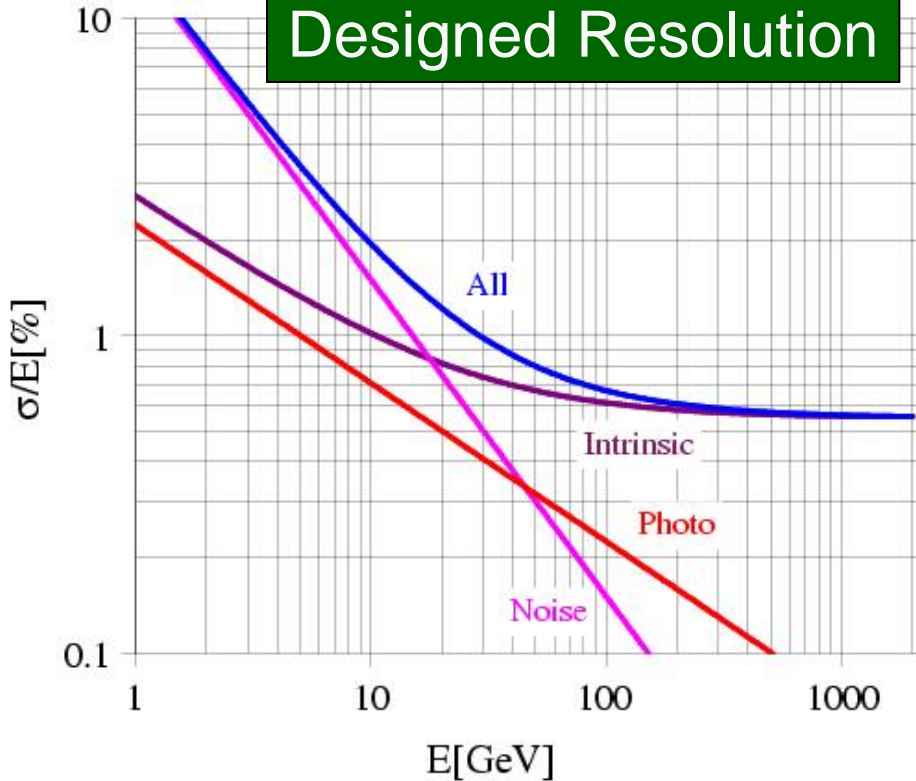





Crystal Degradation *in situ*



L3 BGO degrades 6 – 7% in 7 years

BaBar CsI(Tl): 1 - 3 % per year

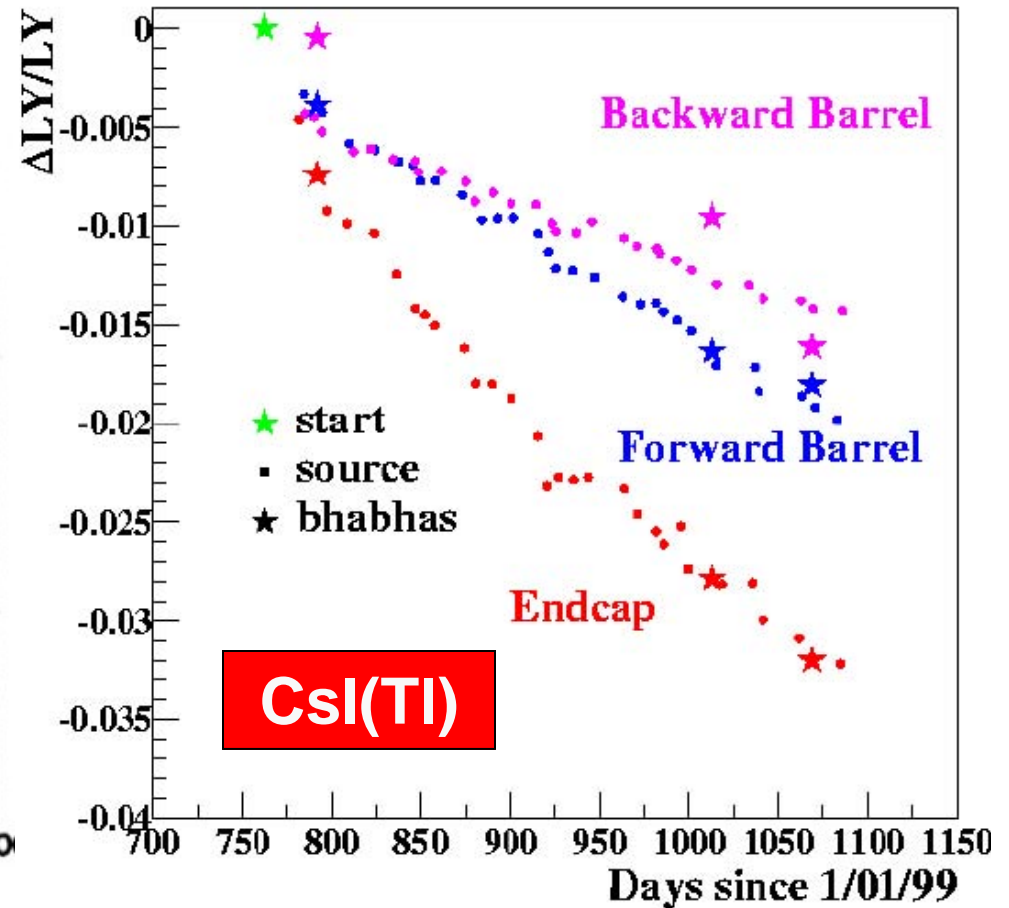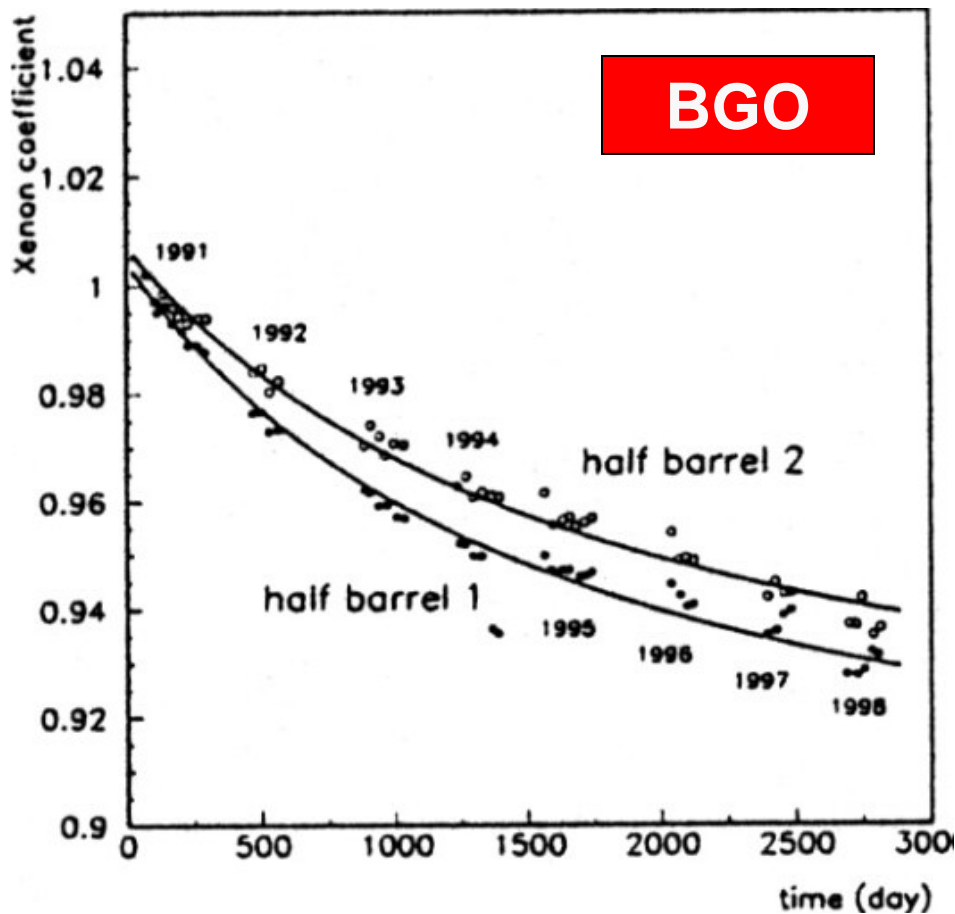



Effects of Radiation Damage



- Induced absorption caused by color center formation:
 - reduced light attenuation length and thus light output, and maybe
 - degraded of light response uniformity (LRU).
- Induced phosphorescence:
 - increase readout noise.
- Reduced scintillation light yield:
 - reduce light output and degrade light response uniformity.



Item	CsI(Tl)	CsI	BaF ₂	BGO	PbWO ₄
Color Centers	Yes	Yes	Yes	Yes	Yes
Fluorescence	Yes	Yes	Yes	Yes	Yes
Scintillation	No	No	No	No	No
Recover @RT	Slow	Slow	No	Yes	Yes
Dose Rate Dependence	No	No	No	Yes	Yes
Thermal Annealing	No/Yes	No/Yes	Yes	Yes	Yes
Optical Bleaching	No/Yes	No/Yes	Yes	Yes	Yes



Radiation Induced Absorption



Measured with Hitachi U-3210 Photospectrometer

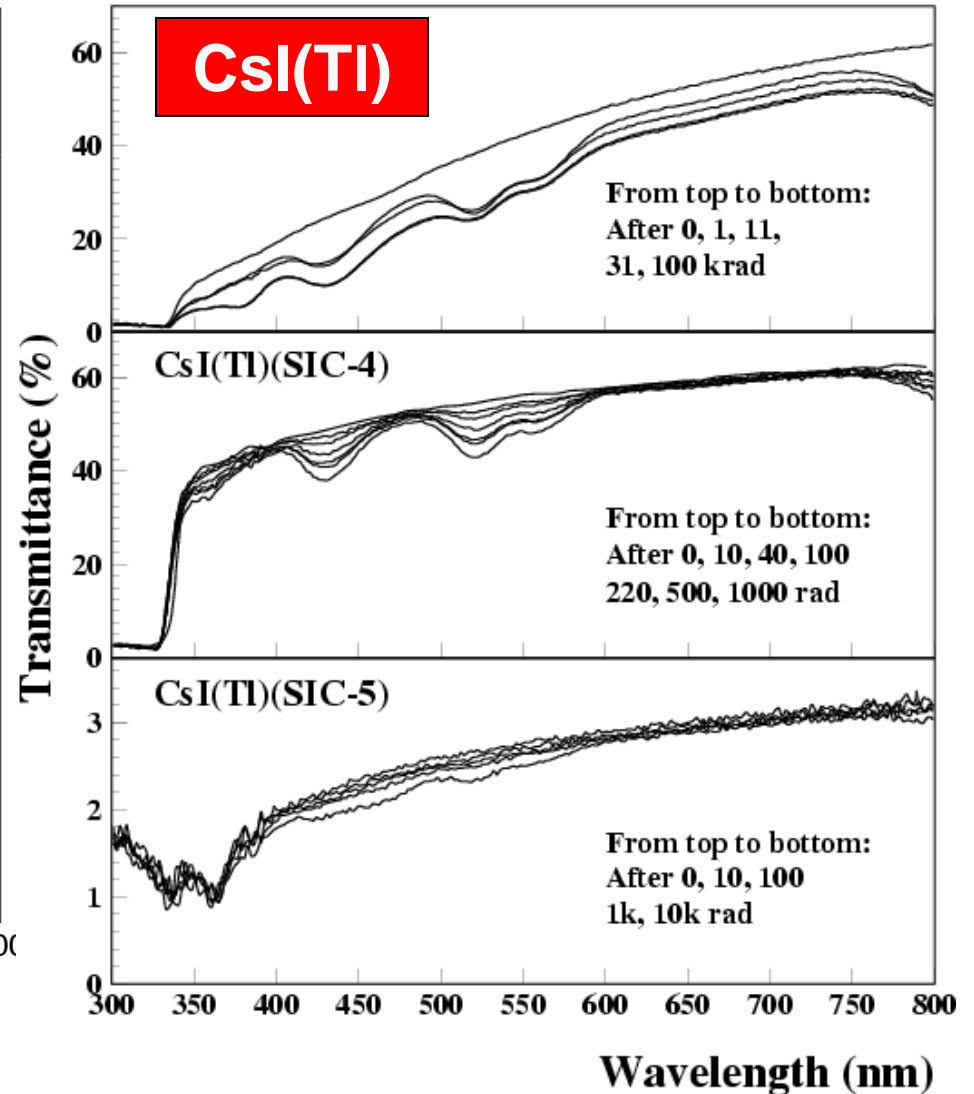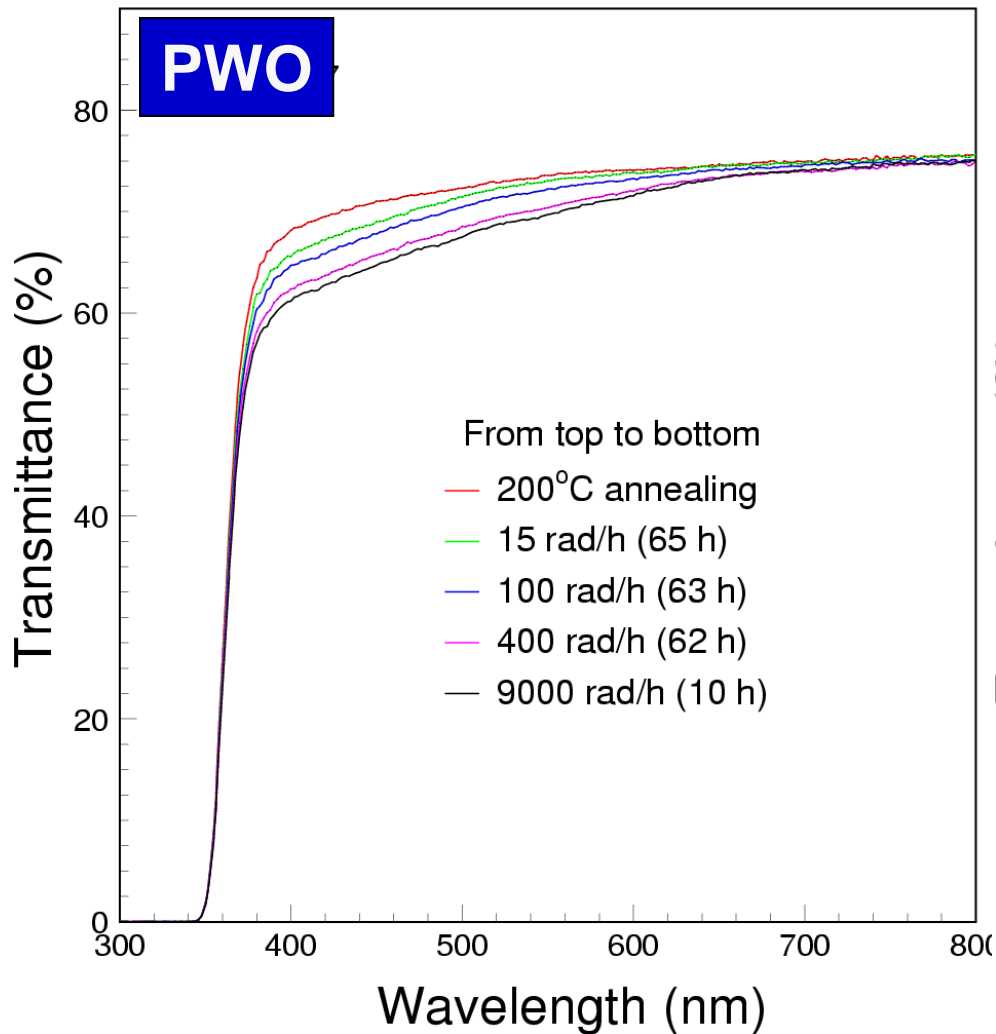




SIMS Study & CsI(Tl) Improvement



Secondary Ion Mass Spectroscopy revealed depth profile of oxygen contamination; Oxygen control improves CsI(Tl) quality

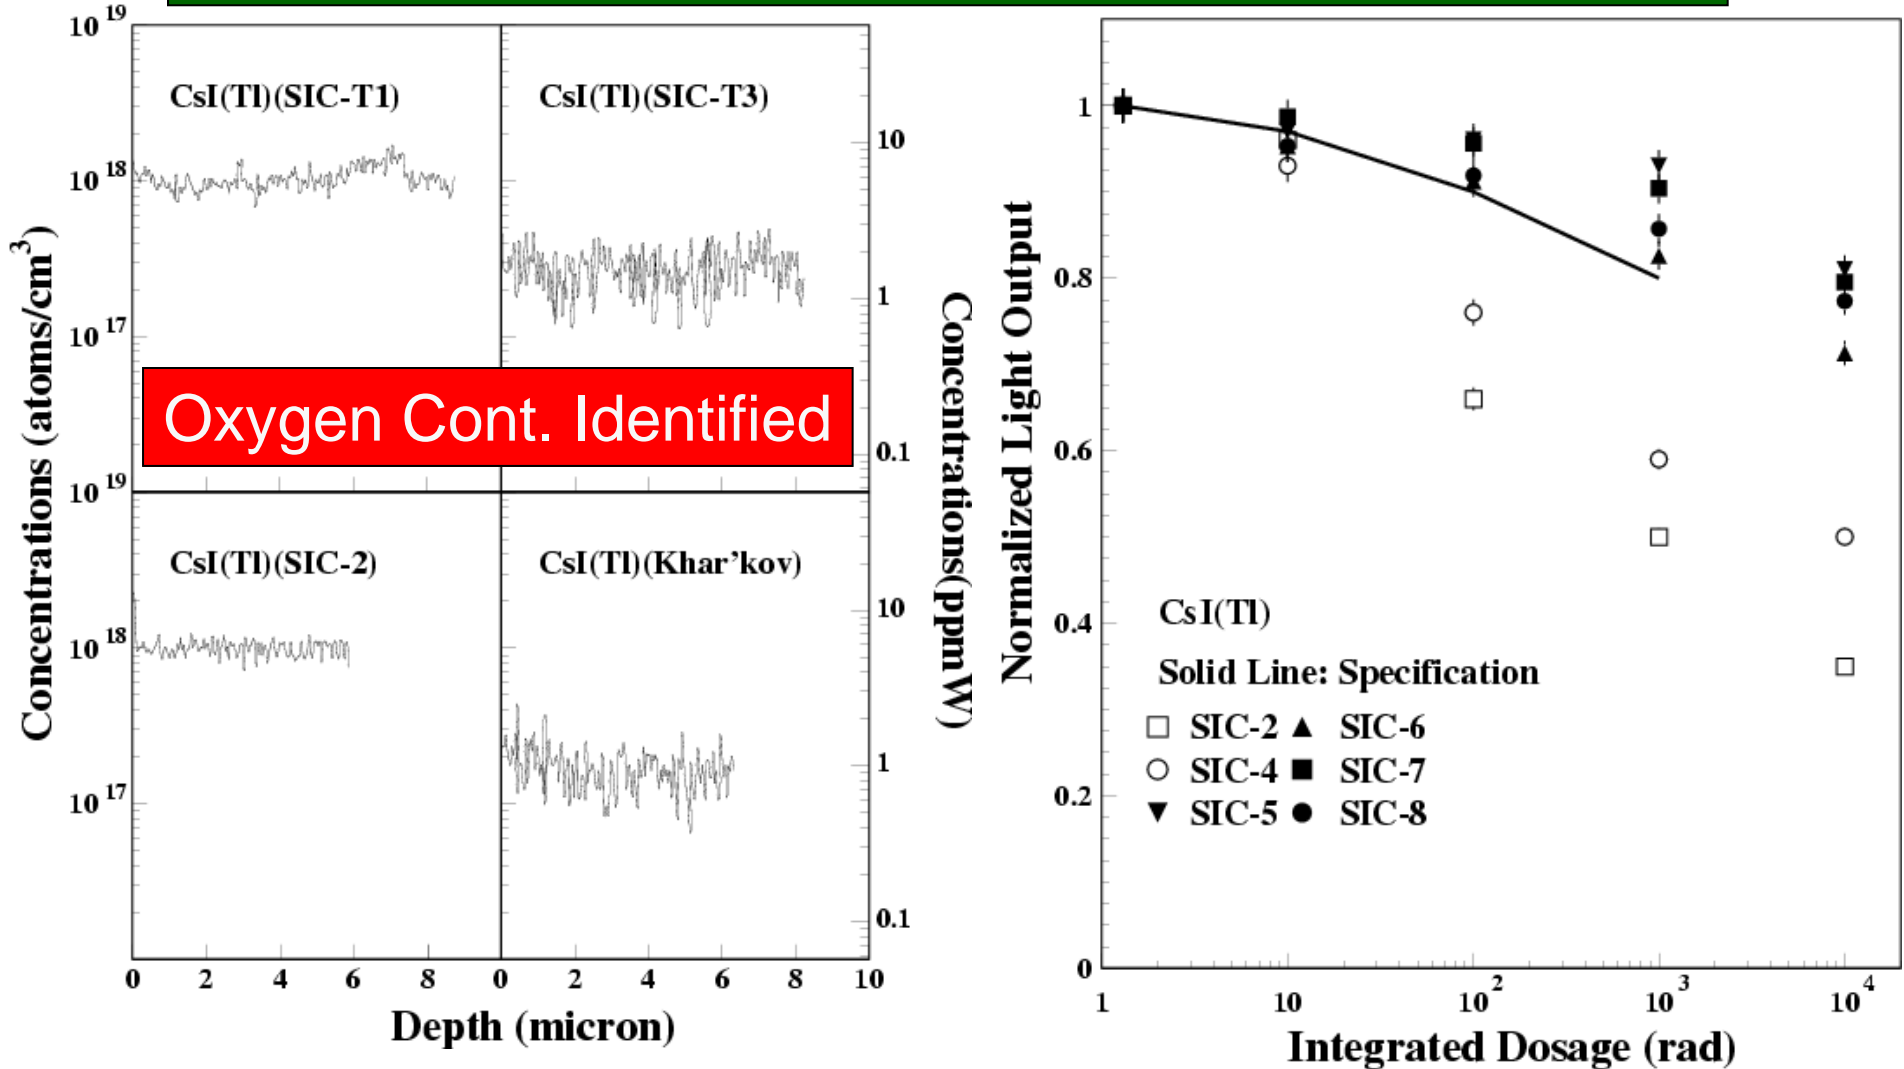




TEM/EDS Study on PWO Crystals




TOPCON-002B scope, 200 kV, 10 uA, 5 to 10 nm black spots identified
JEOL JEM-2010 scope and Link ISIS EDS localized Stoichiometry Analysis

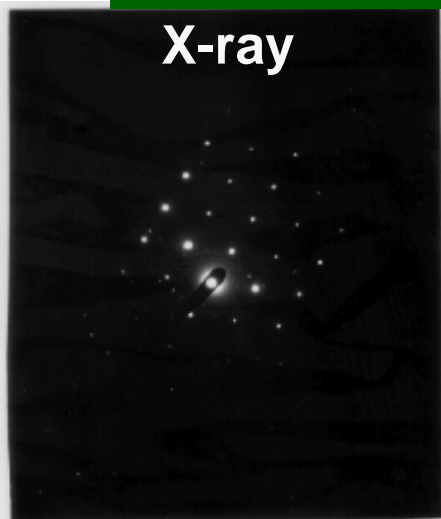


X-ray



Good PWO

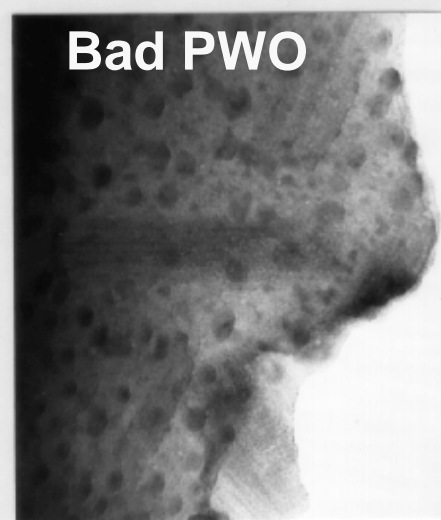

Bad PWO

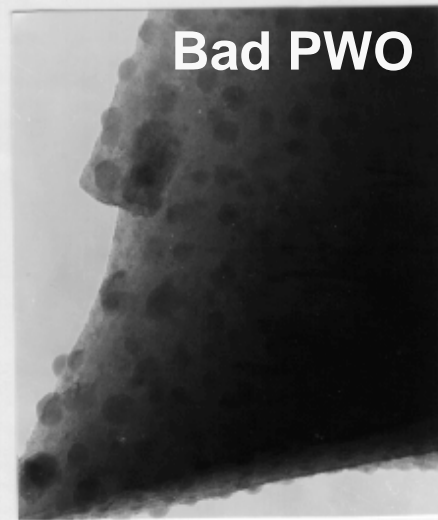

Bad PWO

Atomic Fraction (%) in $PbWO_4$

As Grown Sample

Element	Black Spot	Peripheral	Matrix ₁	Matrix ₂
O	1.5	15.8	60.8	63.2
W	50.8	44.3	19.6	18.4
Pb	47.7	39.9	19.6	18.4

The Same Sample after Oxygen Compensation

Element	Point ₁	Point ₂	Point ₃	Point ₄
O	59.0	66.4	57.4	66.7
W	21.0	16.5	21.3	16.8
Pb	20.0	17.1	21.3	16.5

Oxygen Vacancies Identified



BGO/PWO Quality Improvement





Nucl. Instr. and Meth. A302 (1991) 69

Nucl. Instr. and Meth. A480 (2002) 470

BGO damage recovery after 2.5 krad

PWO damage at different dose rate

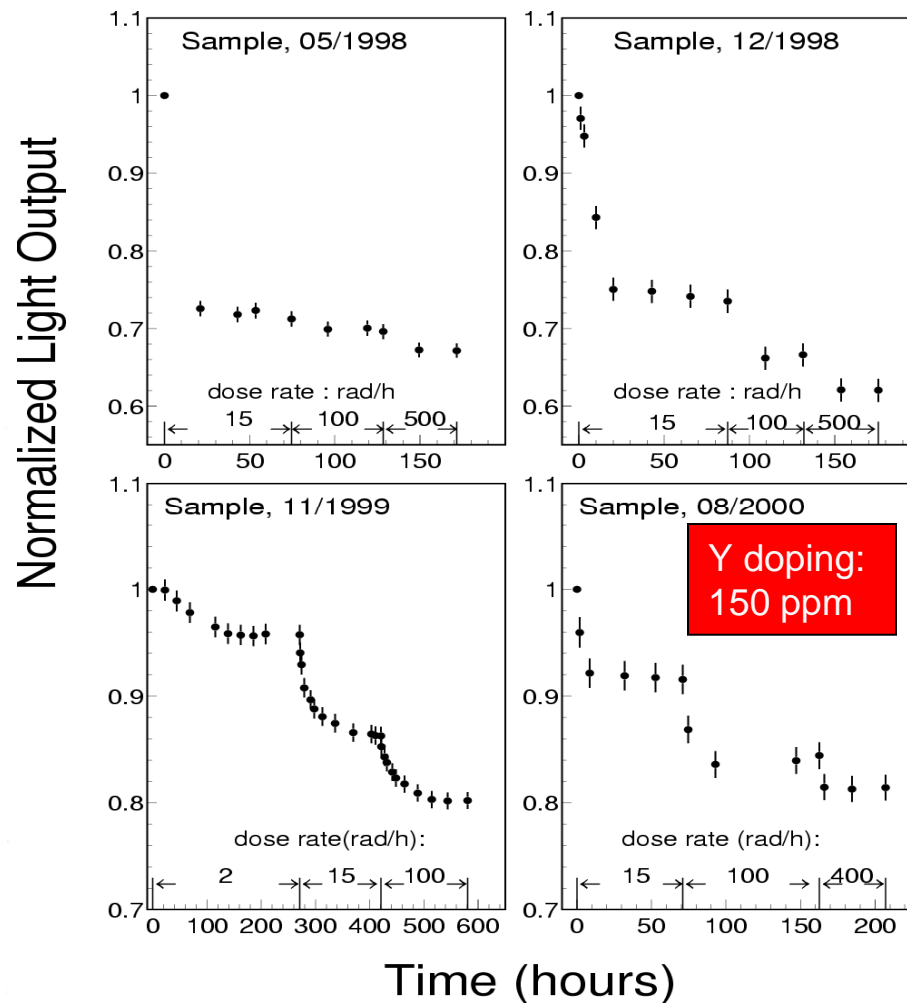
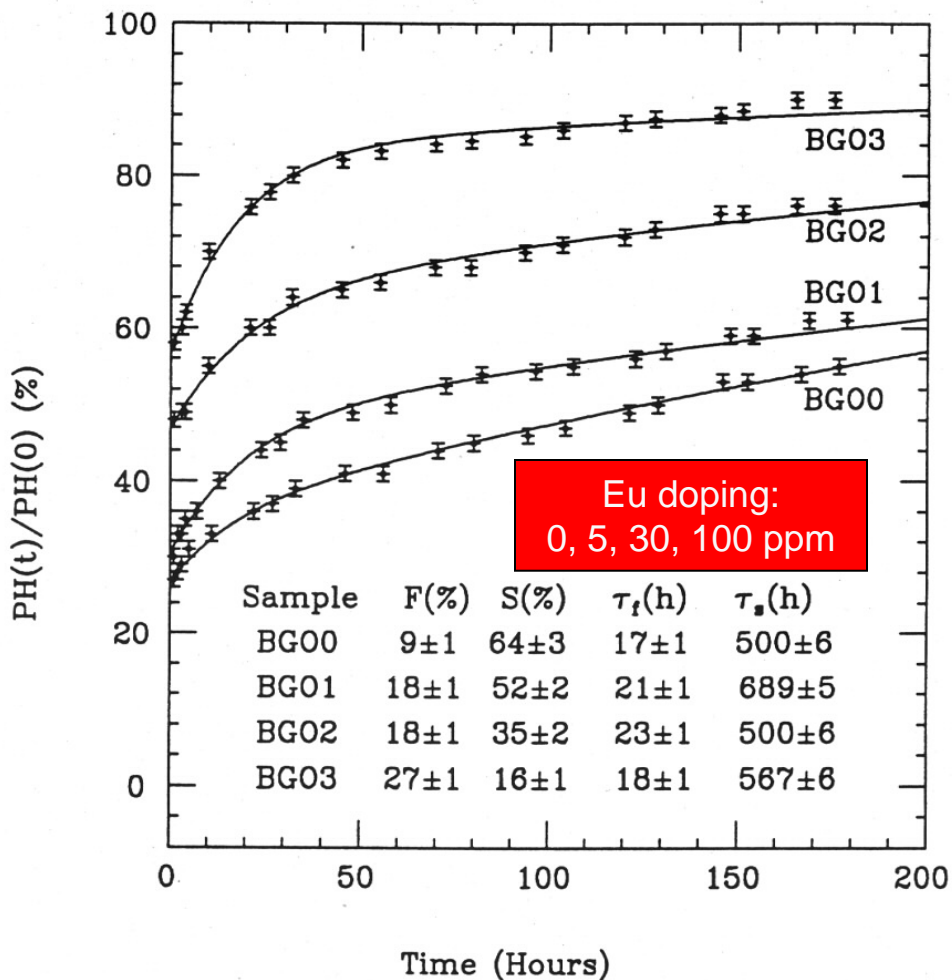




LYSO Transmittance Damage



LT @ 430 nm shows 6 and 3% increase under 2 rad/h, followed by 6 and 5% degradation under 9 krad/h for CPI and SG samples respectively

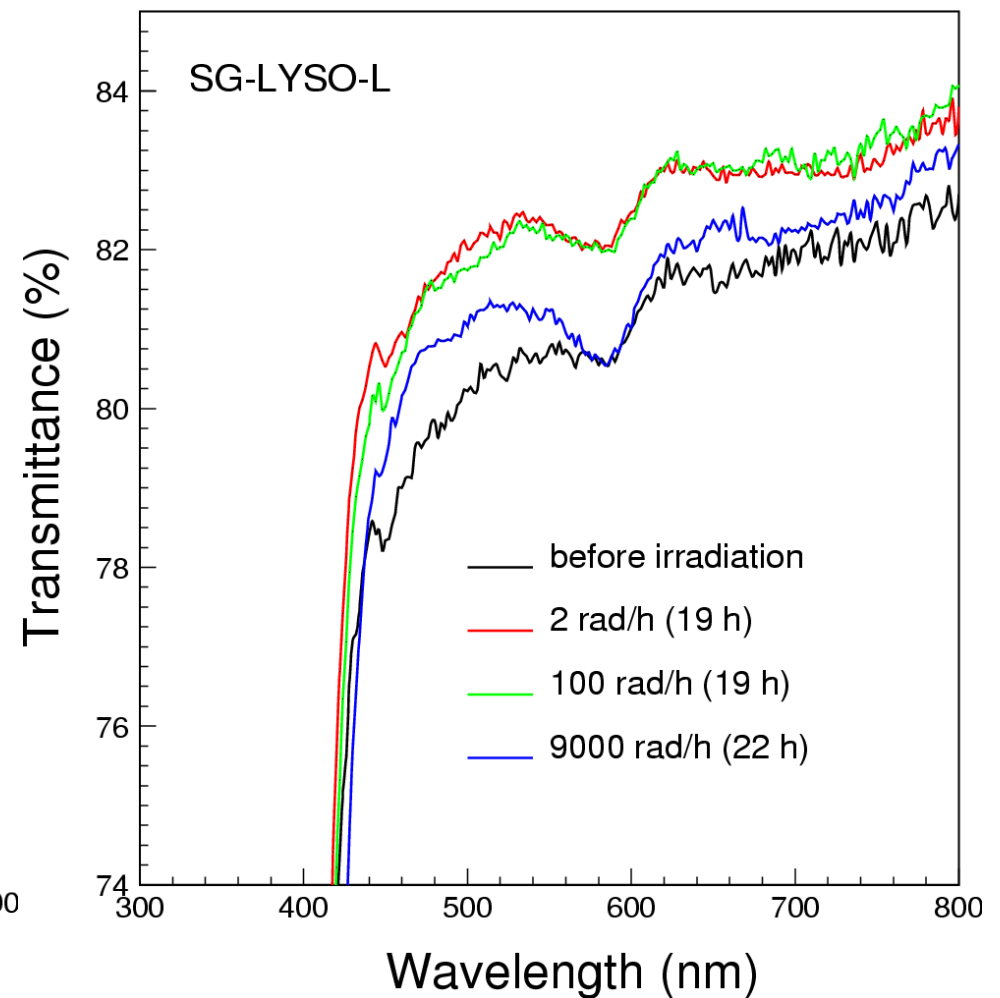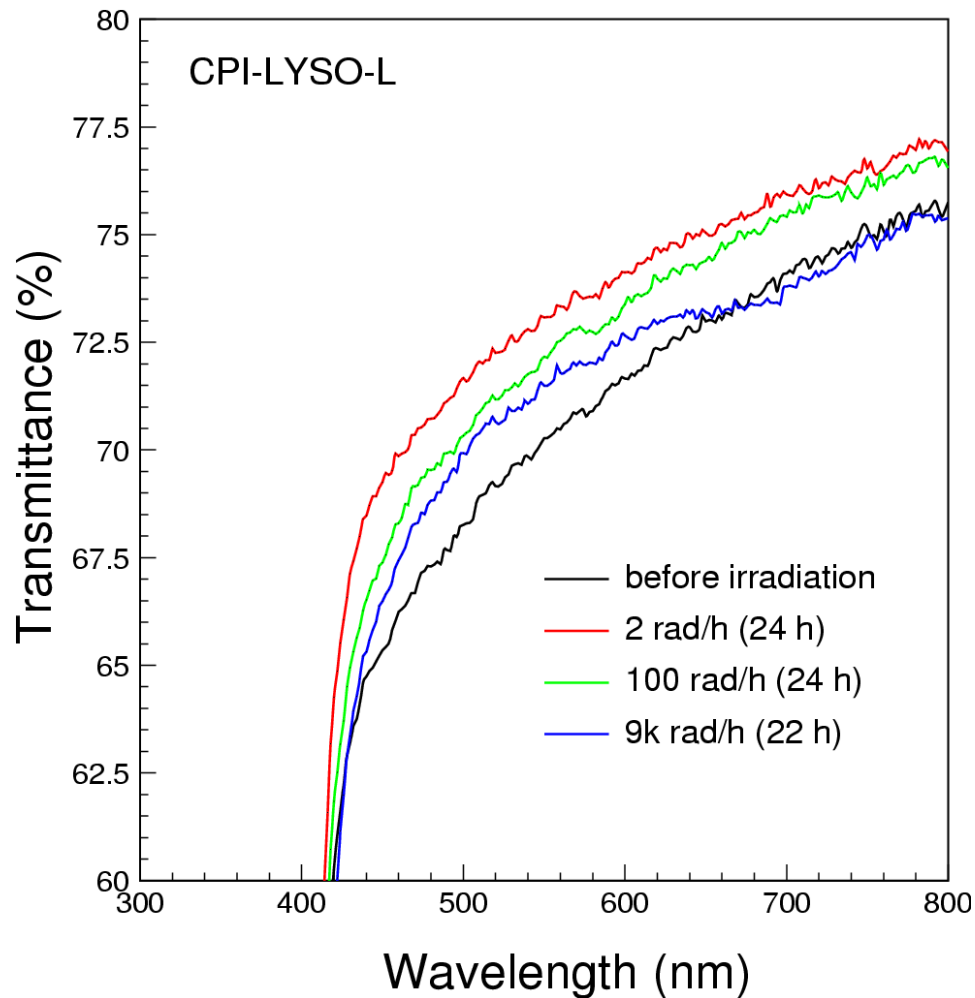



LSO/LYSO ECAL Performance



- Less demanding to the environment because of small temperature coefficient.
- Radiation damage is less an issue as compared to the CMS PWO ECAL.
- A better energy resolution, $\sigma(E)/E$, at low energies than L3 BGO and CMS PWO because of its high light output and low readout noise:

$$2.0\% / \sqrt{E} \oplus 0.5\% \oplus .001/E$$




Summary




- Because of total absorption, precision crystal calorimetry provides the best possible energy and position resolutions for electrons and photons as well as good e/γ identification and reconstruction efficiencies.
- Progress has been made in understanding crystal radiation damage and improving qualities of mass produced crystals.
- An LSO/LYSO crystal calorimeter will provide excellent energy resolution over a large dynamic range down to MeV level for future HEP and NP experiments.



Laser Monitoring for CMS ECAL

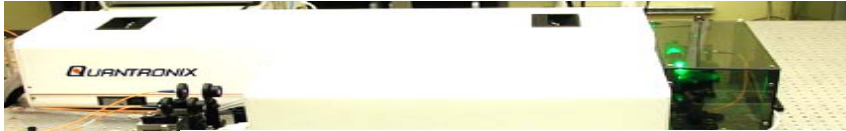

Tracking damage and recovery with laser light

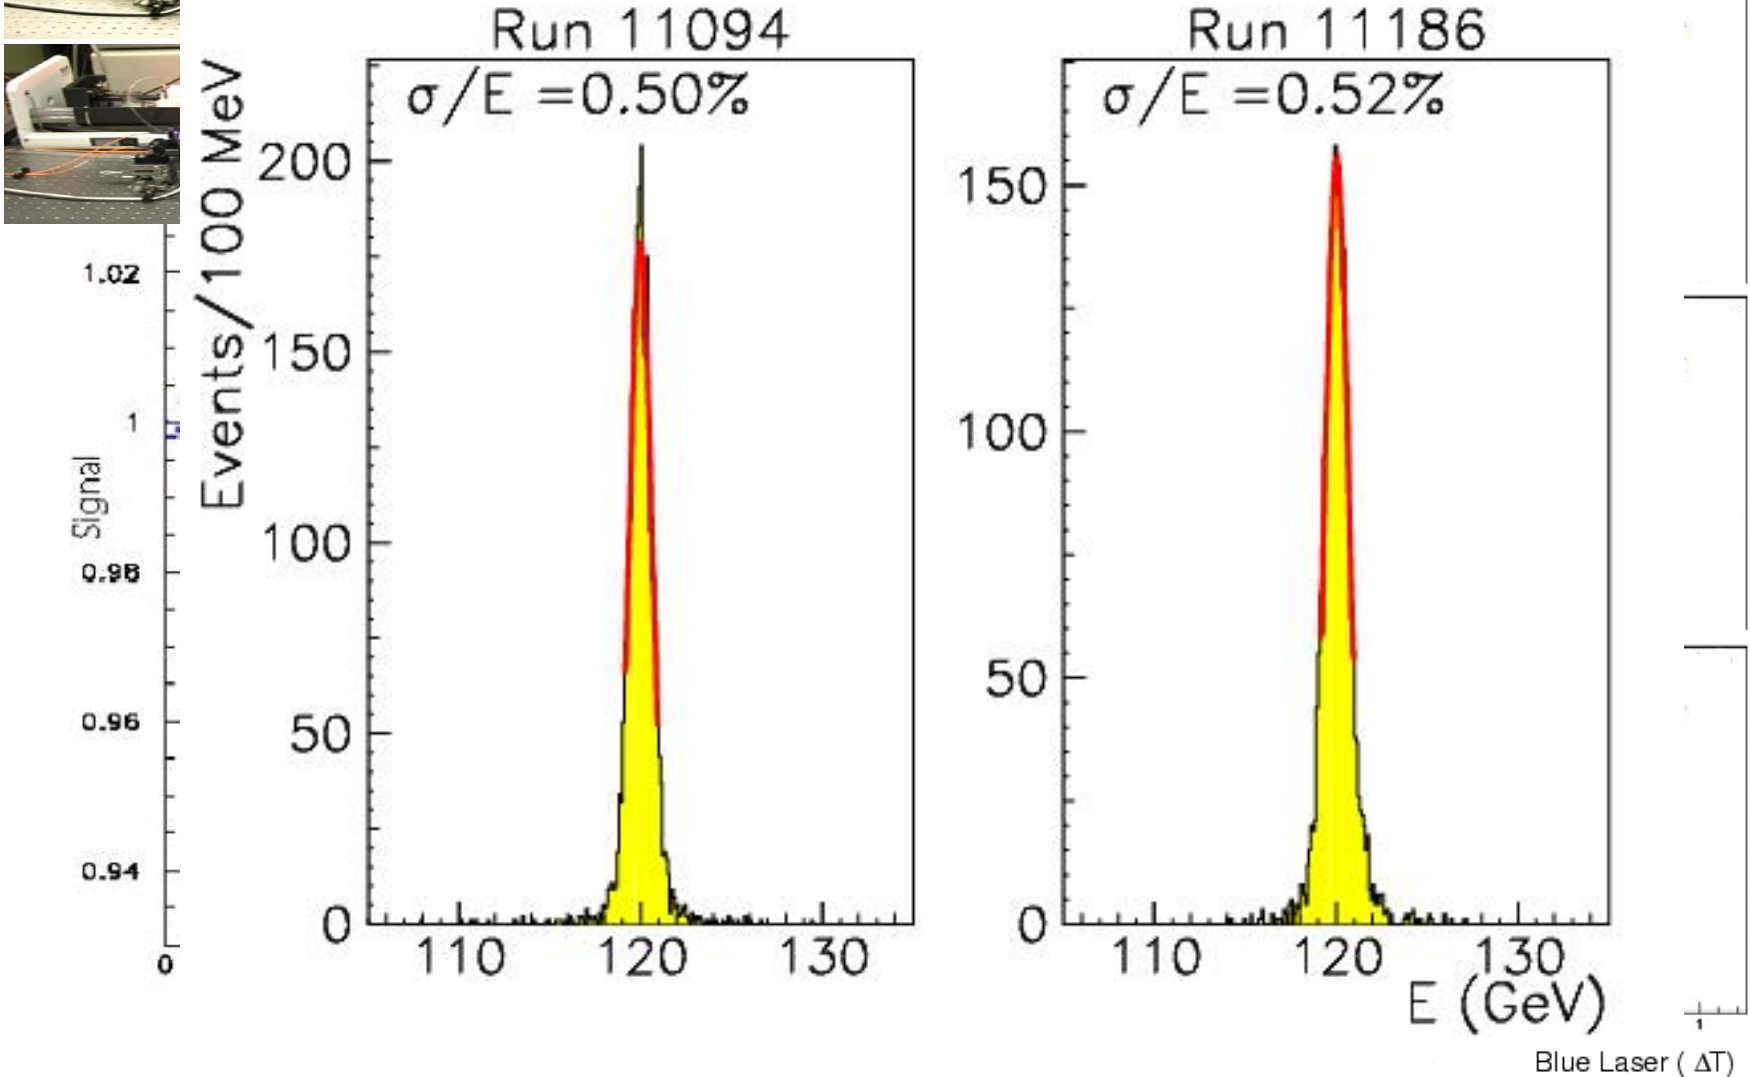




Light Response Uniformity (LRU)




Nucl. Instr. And Meth. A340 (1994) 442

Definition

$$Y = Y_{mid} [1 + \delta(x/x_{mid} - 1)]$$

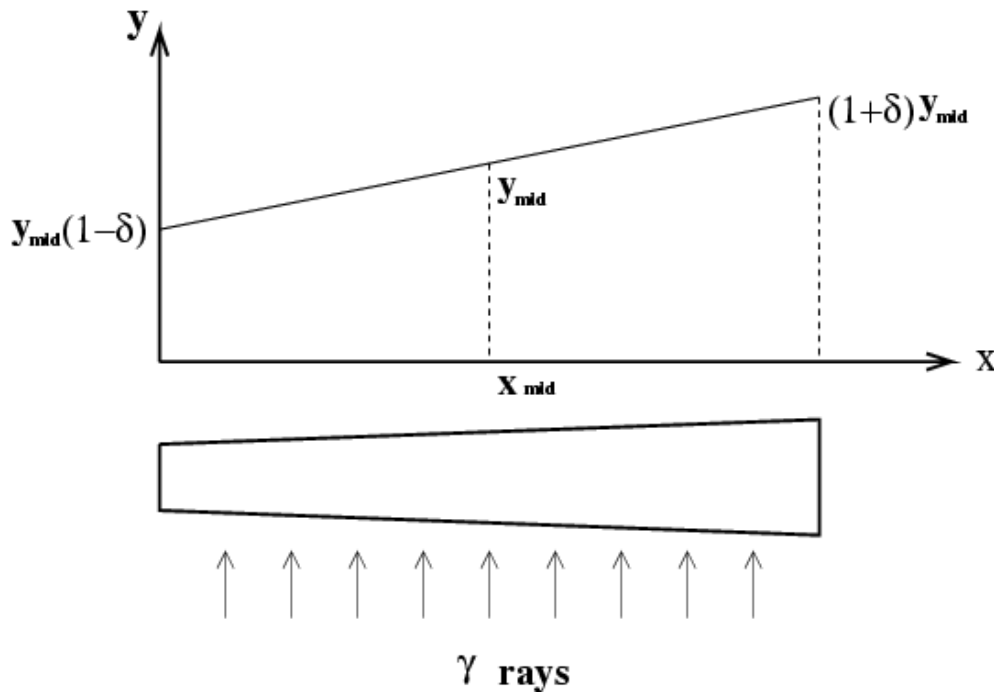

GEANT Simulation

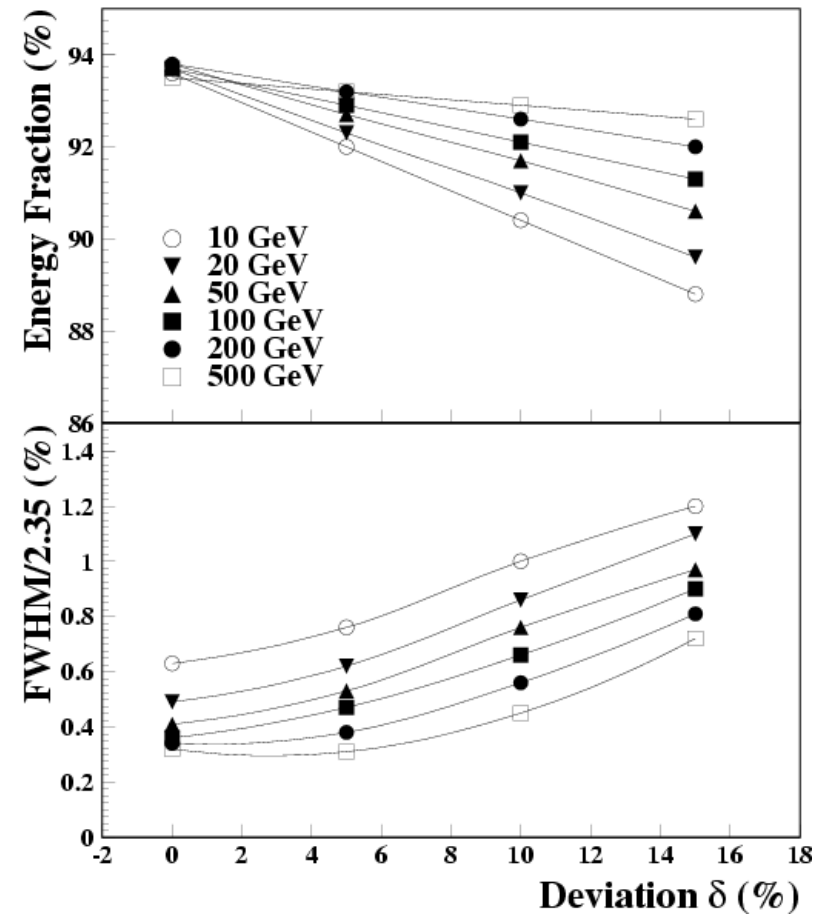


Resolution degradation is not recoverable if LRU is damaged



CMS Specification to the LRU



D. Graham & C. Seez, CMS Note 1996-002

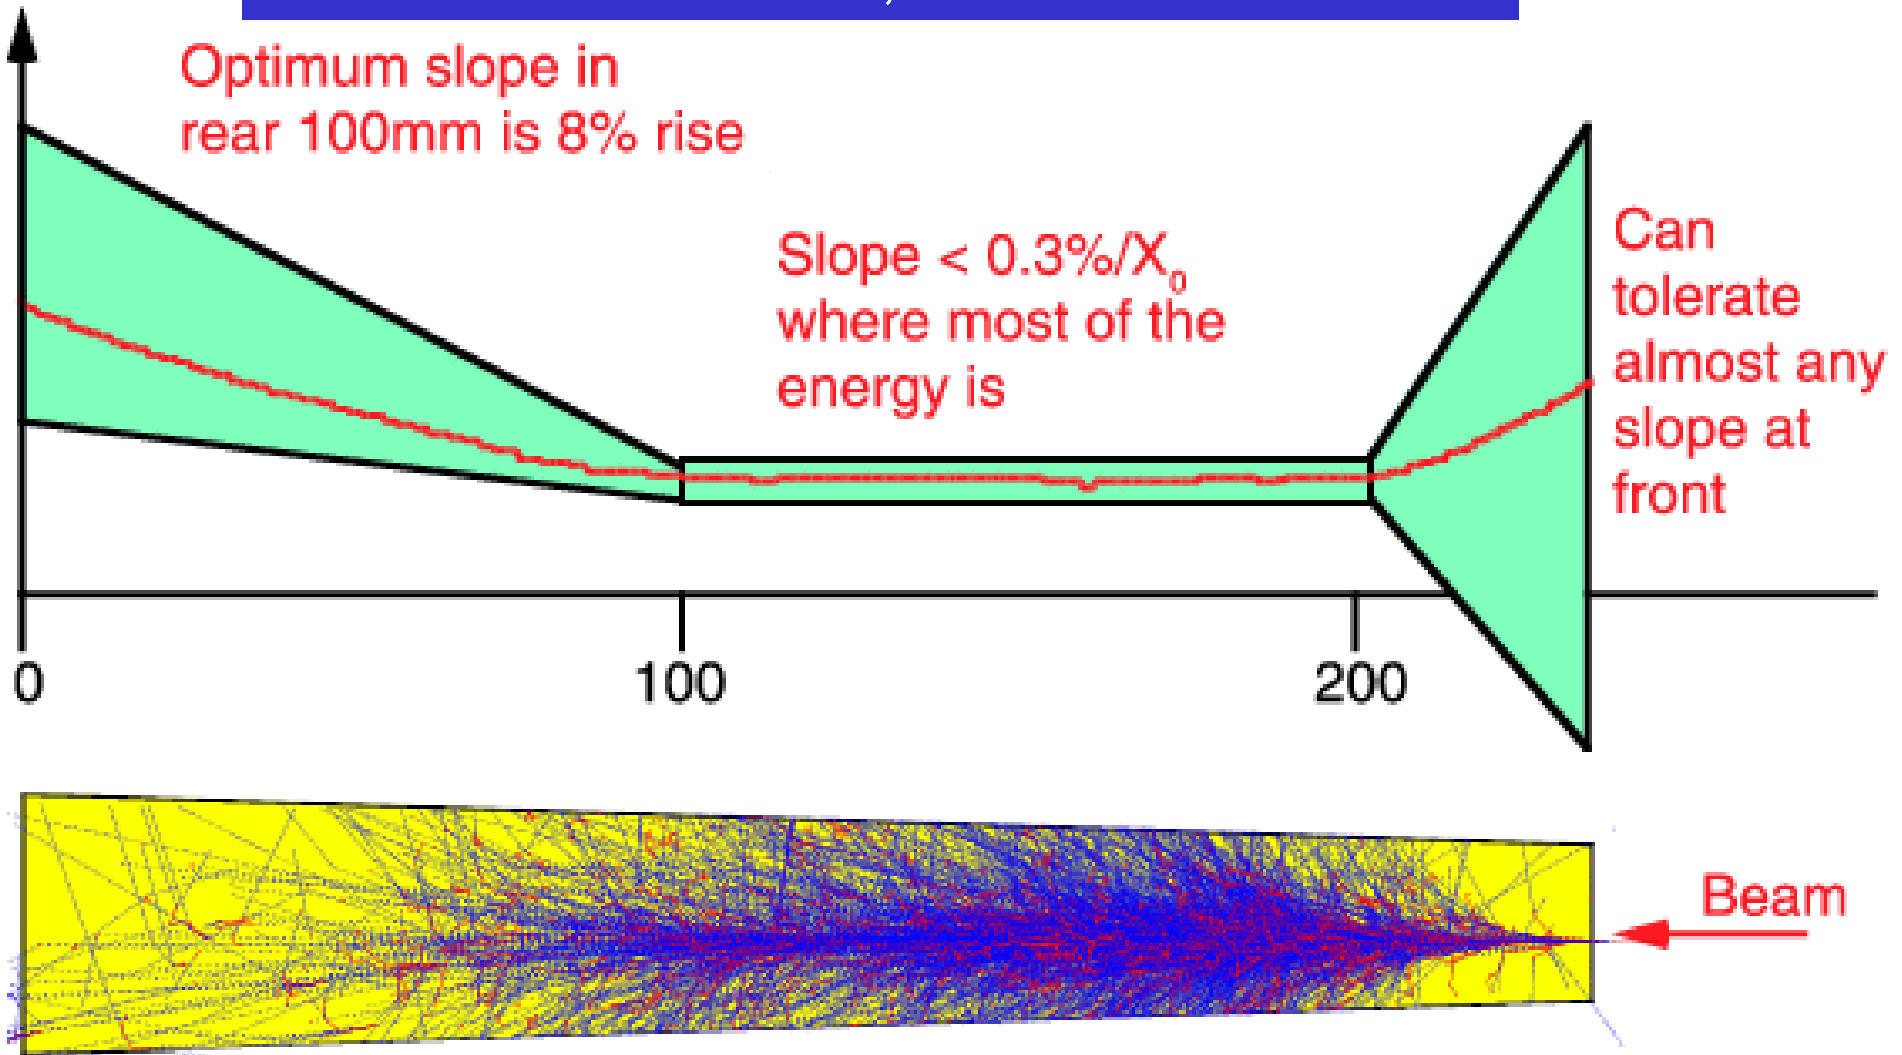



LAL affects LRU



Nucl. Instr. And Meth. A413 (1998) 297

Ray-Tracing simulation for CMS PWO crystals shows no change in LRU if LAL is longer than 3.5 crystal length

Light collection efficiency, fit to a linear function of distance to the small end of the crystal, was determined with two parameters: the light collection efficiency at the middle of the crystal and the uniformity.



LAL (cm)	20	40	60	80	200
Large Area Photo Detector, covering 100% back face					
η_m (%)	9.5 ± 0.2	15.7 ± 0.4	19.2 ± 0.5	21.6 ± 0.6	26.9 ± 0.7
δ (%)	23 ± 1	-4.6 ± 0.8	-11 ± 1	-15 ± 1	-15 ± 1
$\phi 5$ mm Photo Detector, covering 3.7% back face					
η_m (%)	$.38 \pm 0.04$	$.74 \pm 0.08$	1.1 ± 0.1	1.4 ± 0.2	3.0 ± 0.3
δ (%)	23 ± 4	-3.5 ± 0.4	-12 ± 4	-16 ± 4	-17 ± 3
$\frac{\eta_m(\phi 5mm)}{\eta_m(Full)}$ (%)	4.0	4.7	5.7	6.5	11



PWO Radiation Damage




No damage in scintillation mechanism
No damage in resolution if light attenuation length > 1 m

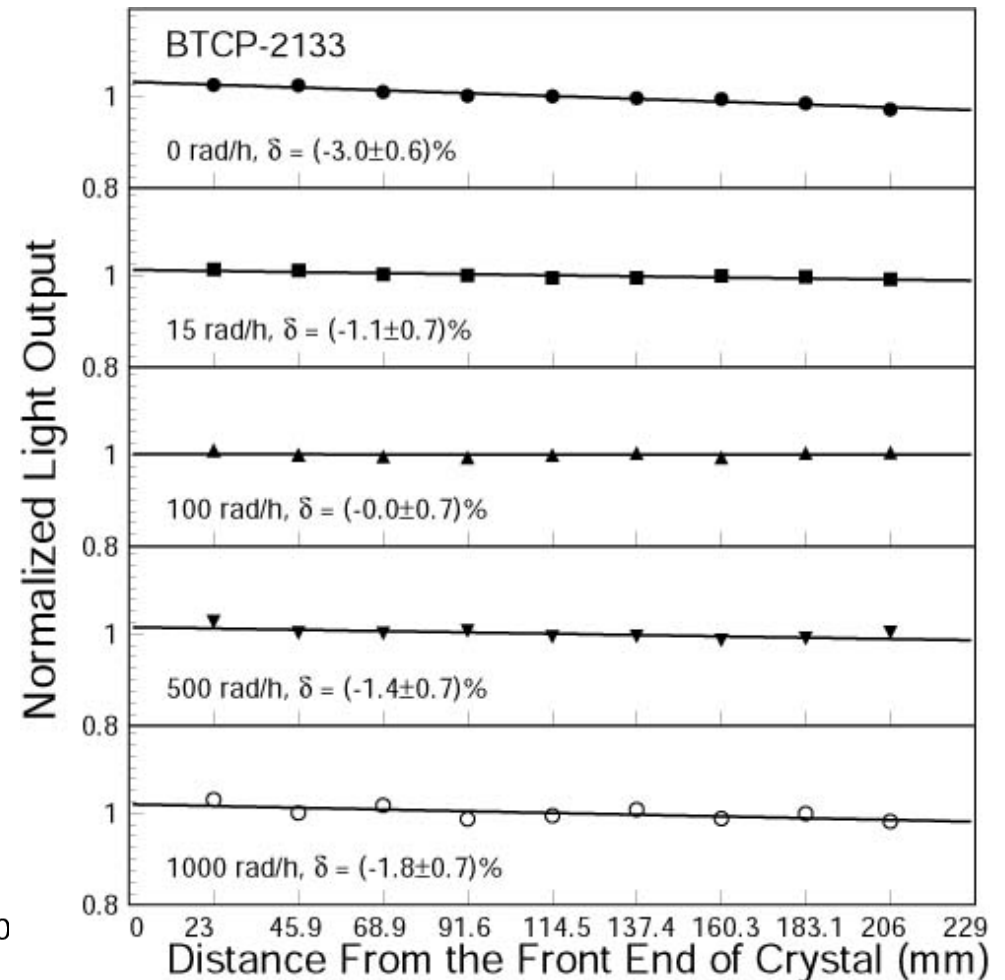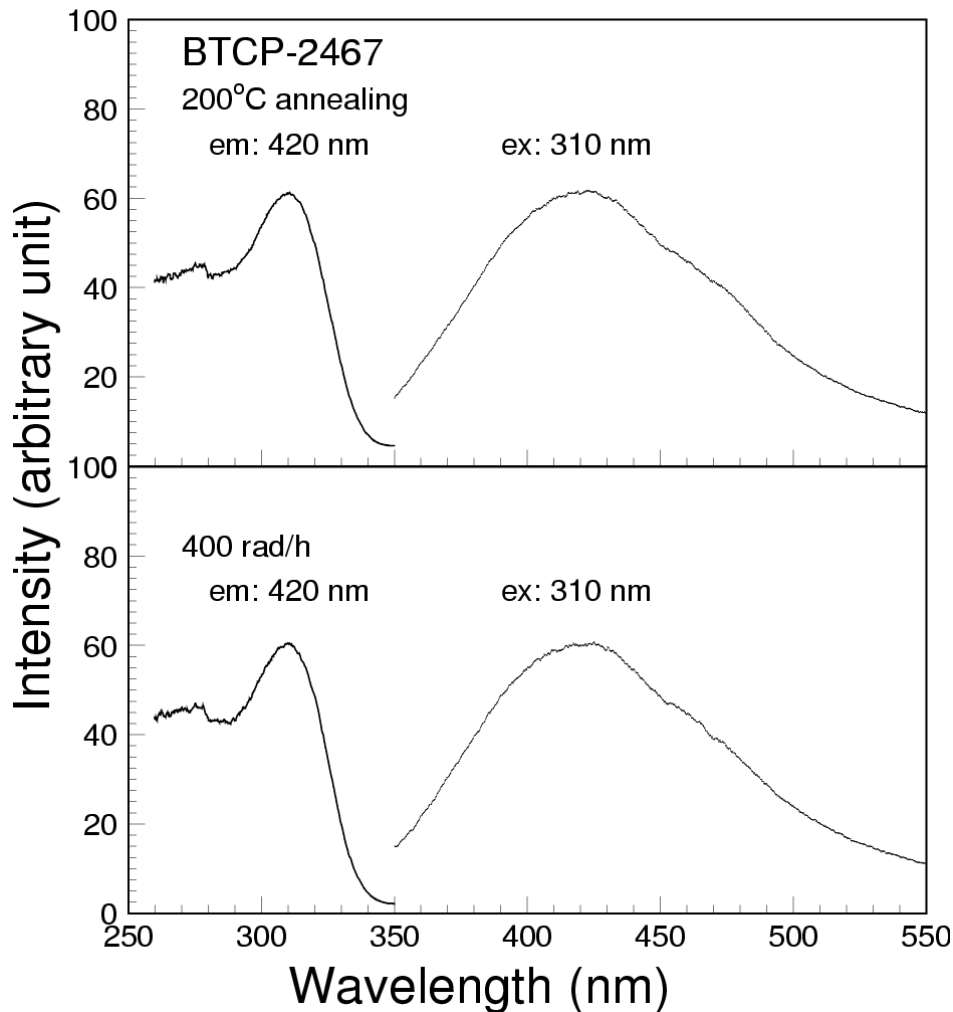



Dose Rate Dependence

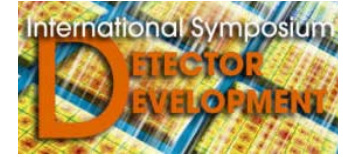


IEEE Trans. Nucl. Sci., Vol. 44 (1997) 468-476

$$dD = \sum_{i=1}^n \{-a_i D_i dt + (D_i^{all} - D_i) b_i R dt\}$$

$$D = \sum_{i=1}^n \left\{ \frac{b_i R D_i^{all}}{a_i + b_i R} [1 - e^{-(a_i + b_i R)t}] + D_i^0 e^{-(a_i + b_i R)t} \right\}$$

- D_i : color center density in units of m^{-1} ;
- D_i^0 : initial color center density;
- D_i^{all} is the total density of trap related to the color center in the crystal;
- a_i : recovery constant in units of hr^{-1} ;
- b_i : damage constant in units of $kRad^{-1}$;
- R : the radiation dose rate in units of $kRad/hr$.

$$D_{eq} = \sum_{i=1}^n \frac{b_i R D_i^{all}}{a_i + b_i R}$$

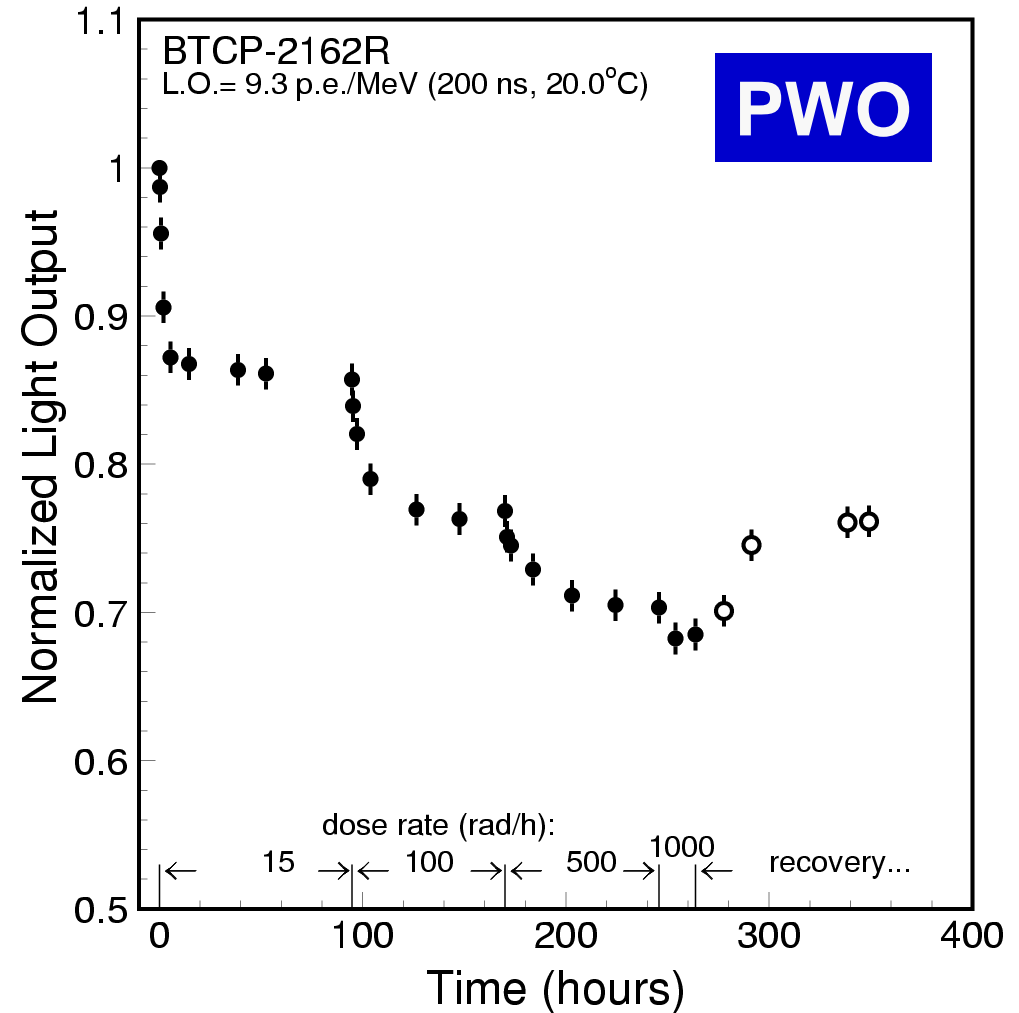




No Dose Rate Dependence




No/slow recovery: no/less dose rate dependence

BaF₂

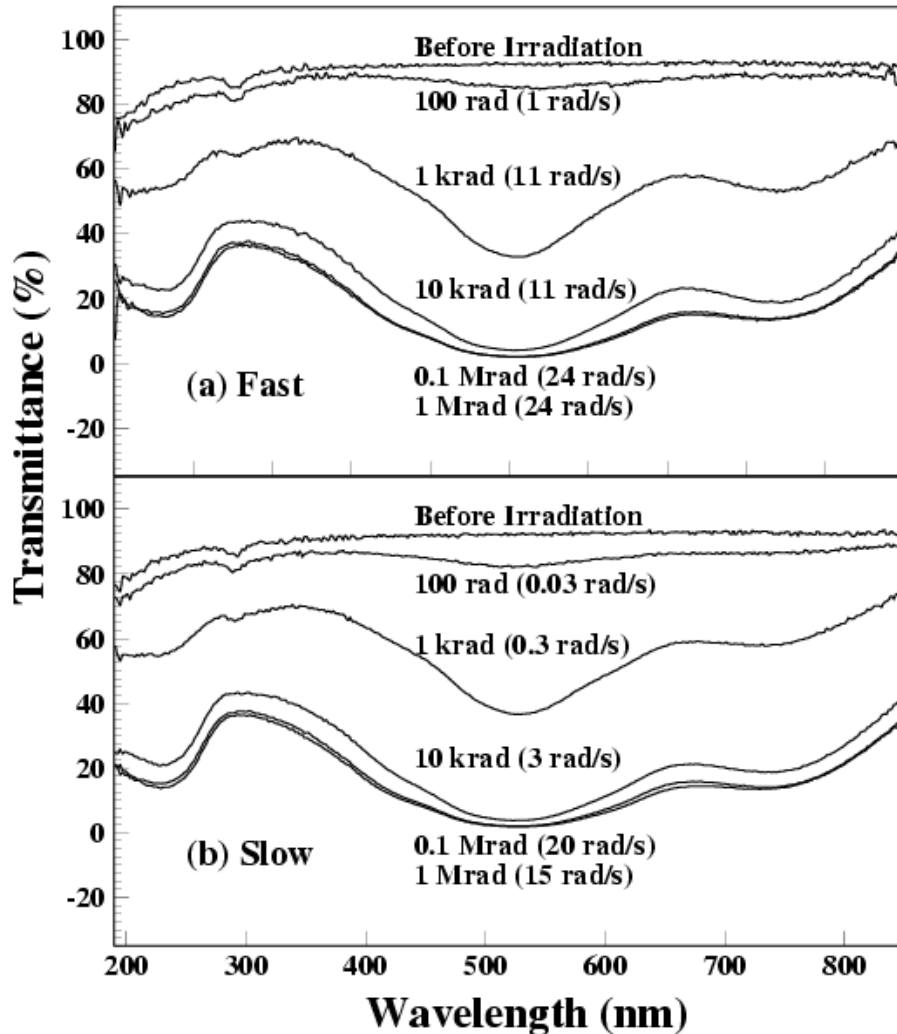

CsI(Tl)

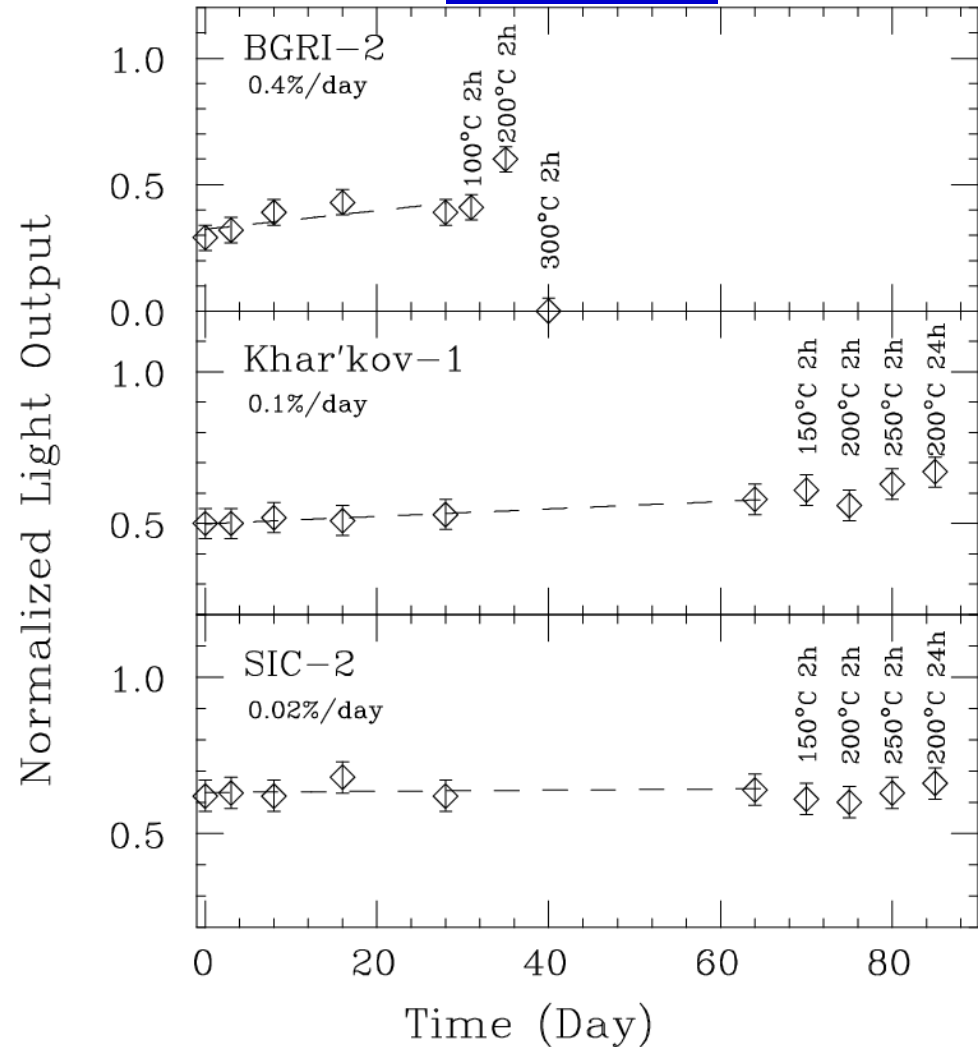



CsI(Tl) Damage Mechanism



Nucl. Instr. And Meth. A340 (1994) 442

- **Oxygen Contamination** is known to cause radiation damage for other alkali halide scintillators. In BaF_2 , for example, hydroxyl (OH^-) may be introduced into crystal through a hydrolysis process, and latter decomposed to interstitial and substitutional centers by radiation through a radiolysis process: $\text{H}_i^0 + \text{O}_s^-$ or $\text{H}_s^- + \text{O}_i^0$, where subscript i and s refer to interstitial and substitutional centers respectively.
- Possible means for trace oxygen identification:
 - **Secondary Ionization Mass Spectroscopy (SIMS);**
 - Gas Fusion (LEGO); and
 - Energy Dispersive x-Ray (EDX).



PWO Radiation Damage Mechanism



Nucl. Instr. And Meth. A413 (1998) 297



- Crystal defects, such as **Oxygen Vacancies**, are known to cause radiation damage for other oxide scintillators. In BGO, for example, three common radiation induced absorption bands at 2.3, 3.0 and 3.8 eV were found in a series of 24 doped samples, indicating defect-related color centers.
- Possible means for oxygen vacancy identification:
 - Electron Paramagnetic Resonance (ESR) and Electron-Nuclear Double Resonance (ENDOR);
 - **Transmission Electron Microscopy (TEM)/Energy Dispersion Spectrometry (EDS); and**
 - A pragmatic way: Oxygen Compensation by Post-Growing Annealing in Oxygen Rich Atmosphere.



Mass Produced PWO Crystals





All samples: EWRIAC $< 1 \text{ m}^{-1}$ up to 400 rad/h
Rigorous QC required to qualify CMS endcap crystals

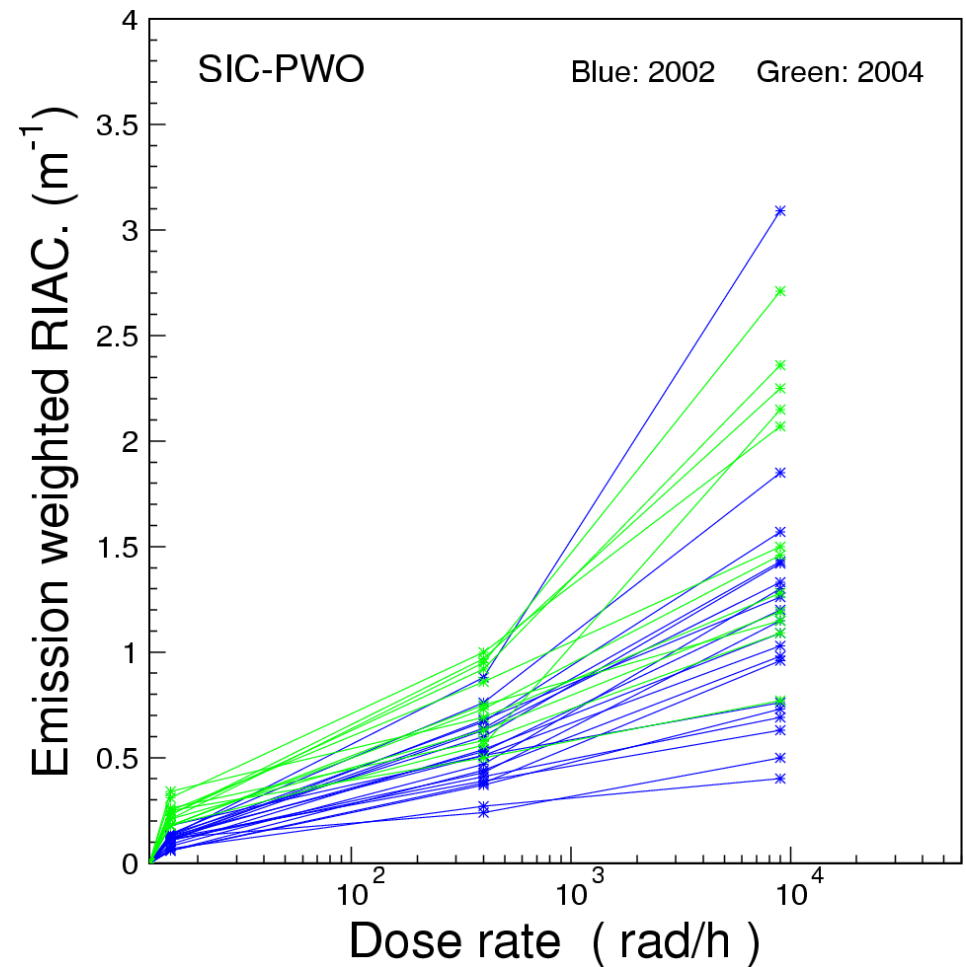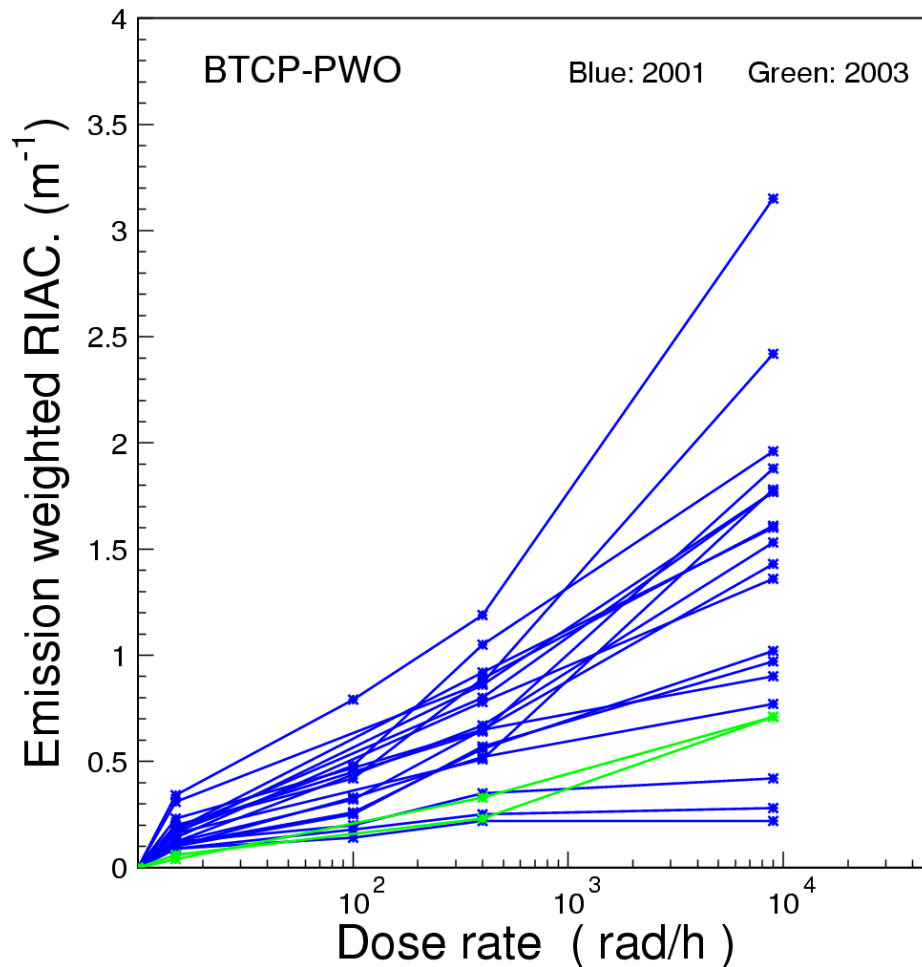



$\delta LO/LO$ versus $\delta LT/LT$ @ 100 rad/h

Strong correlation: Slope = 4.96

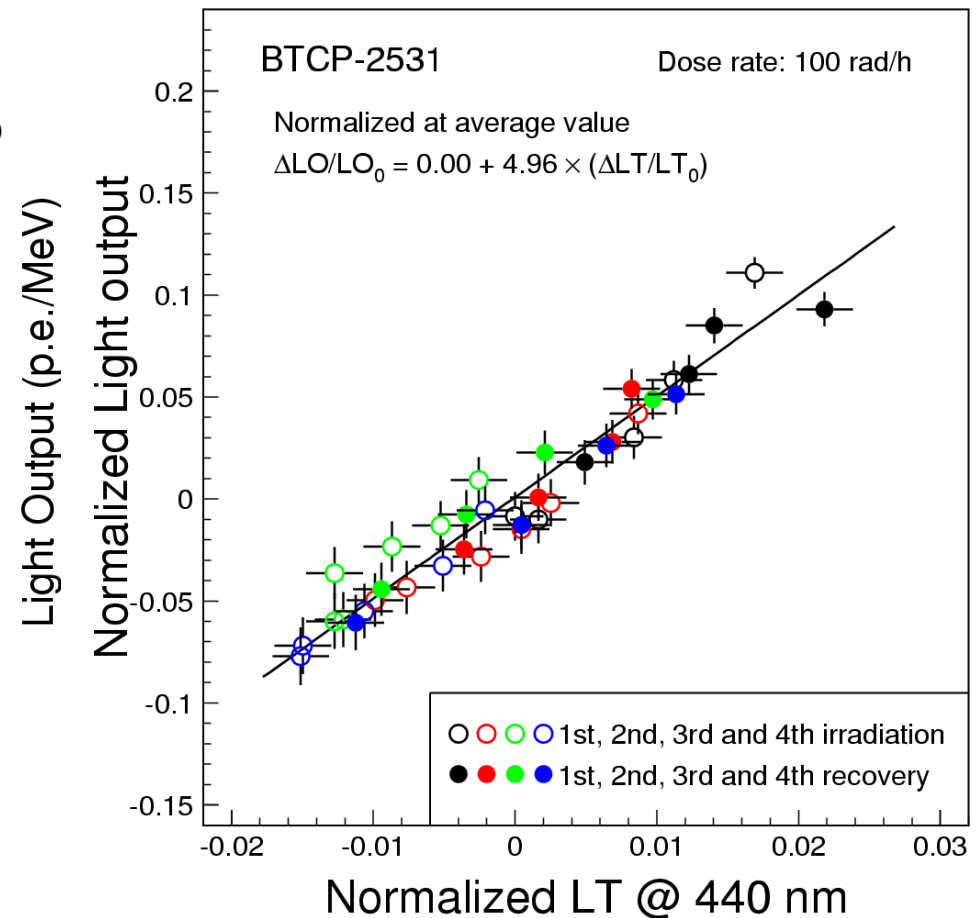
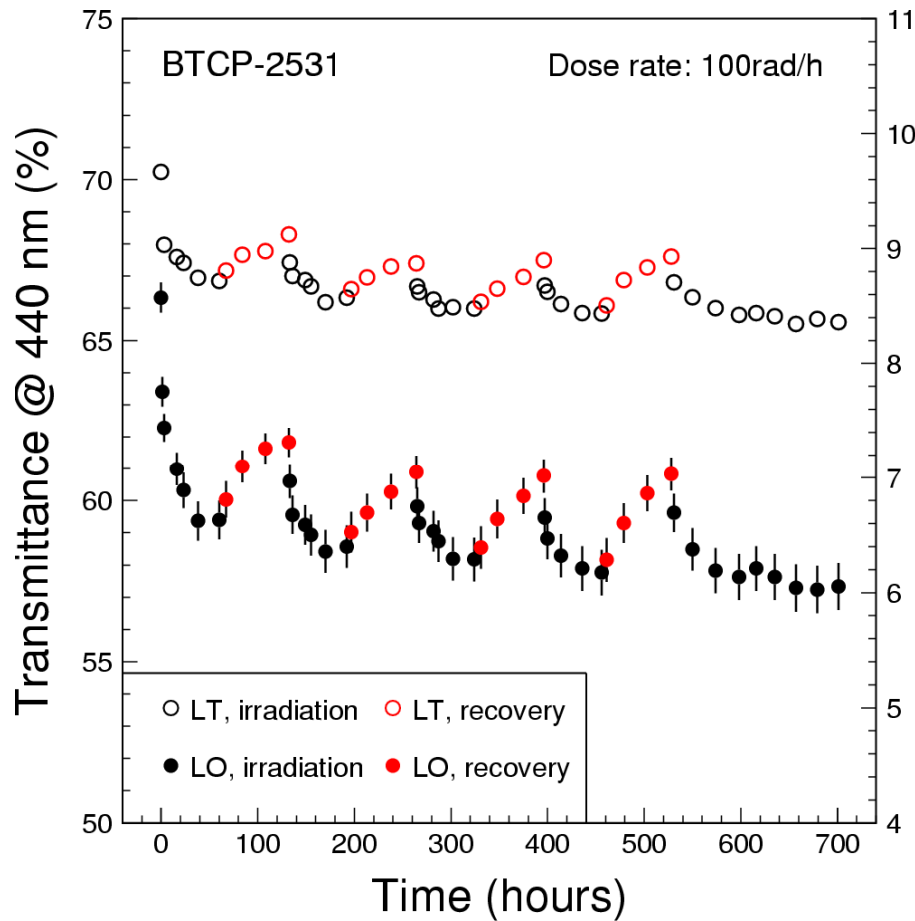




$\delta LO/LO$ versus $\delta LT/LT$ @ 100 rad/h



Strong correlation: Slope = 3.31

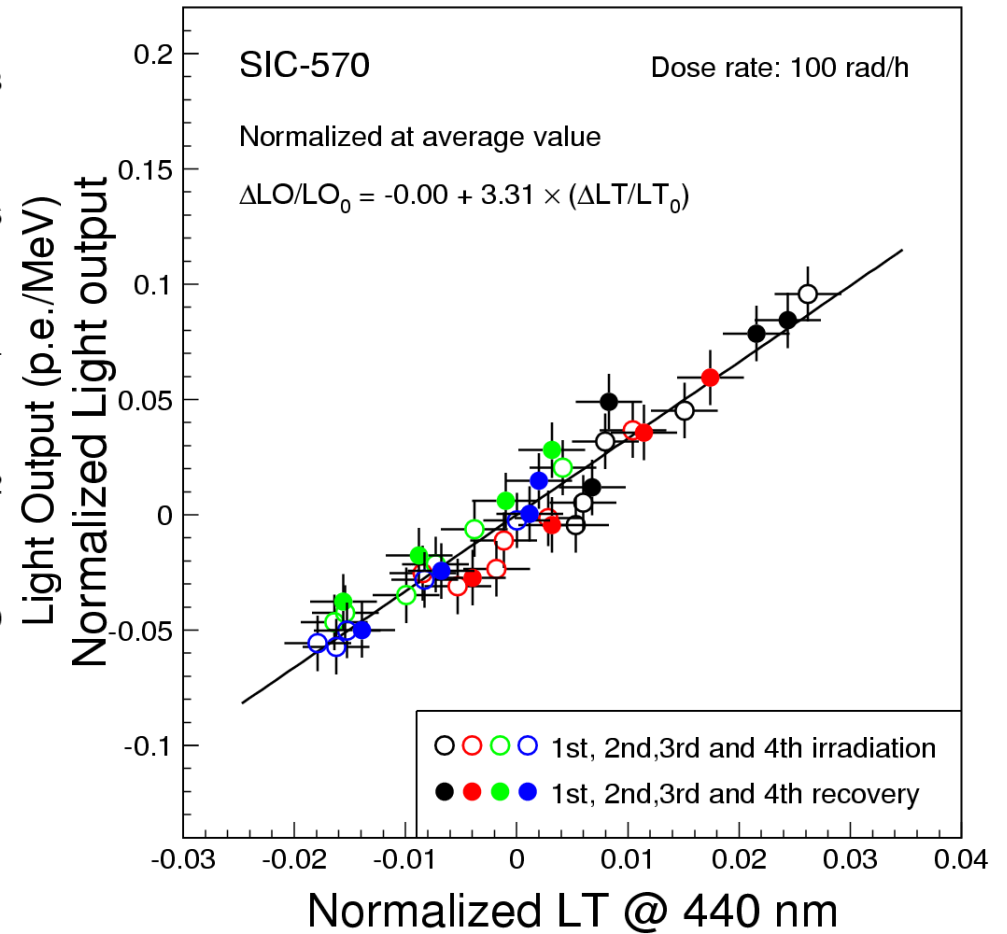
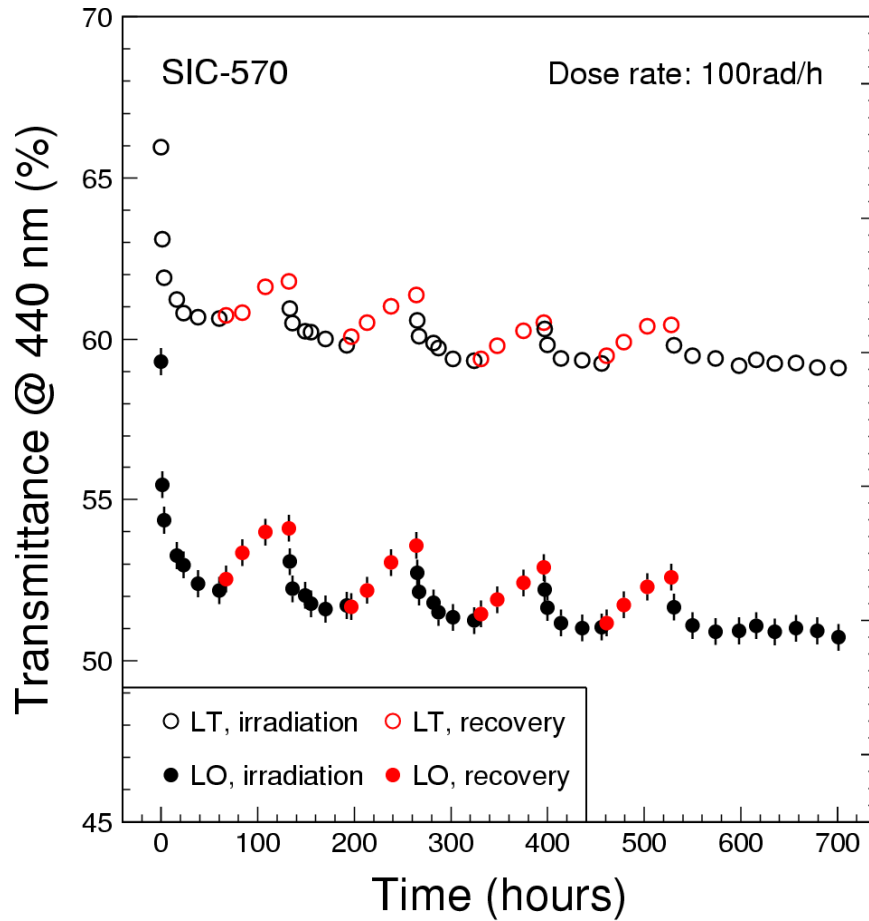




$\delta LO/LO$ versus $\delta LT/LT$ @ 400 rad/h



Strong correlation: Slope = 4.39

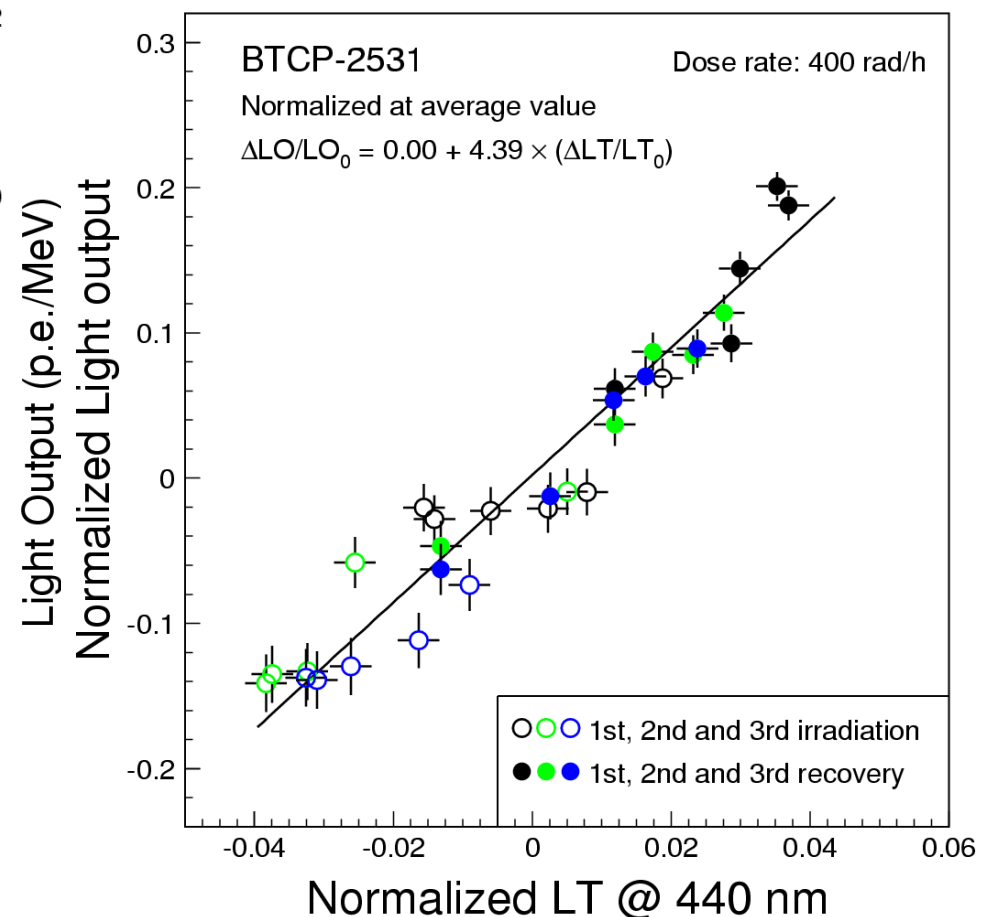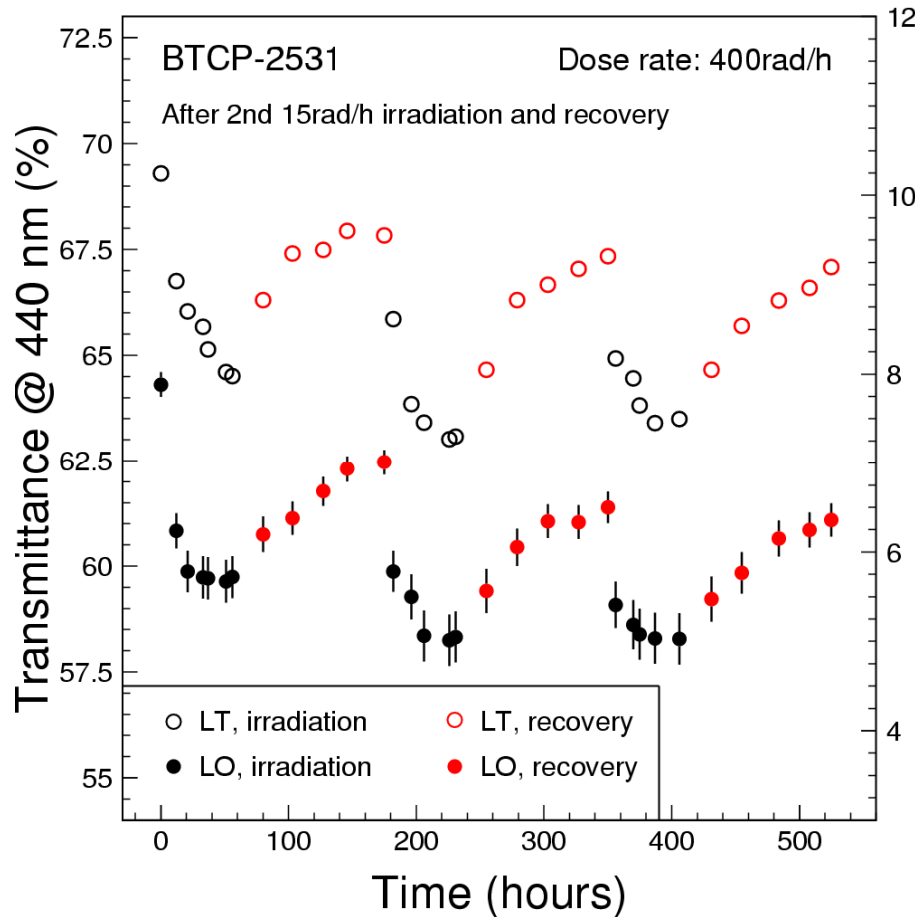




$\delta LO/LO$ versus $\delta LT/LT$ @ 400 rad/h



Strong correlation: Slope = 2.81


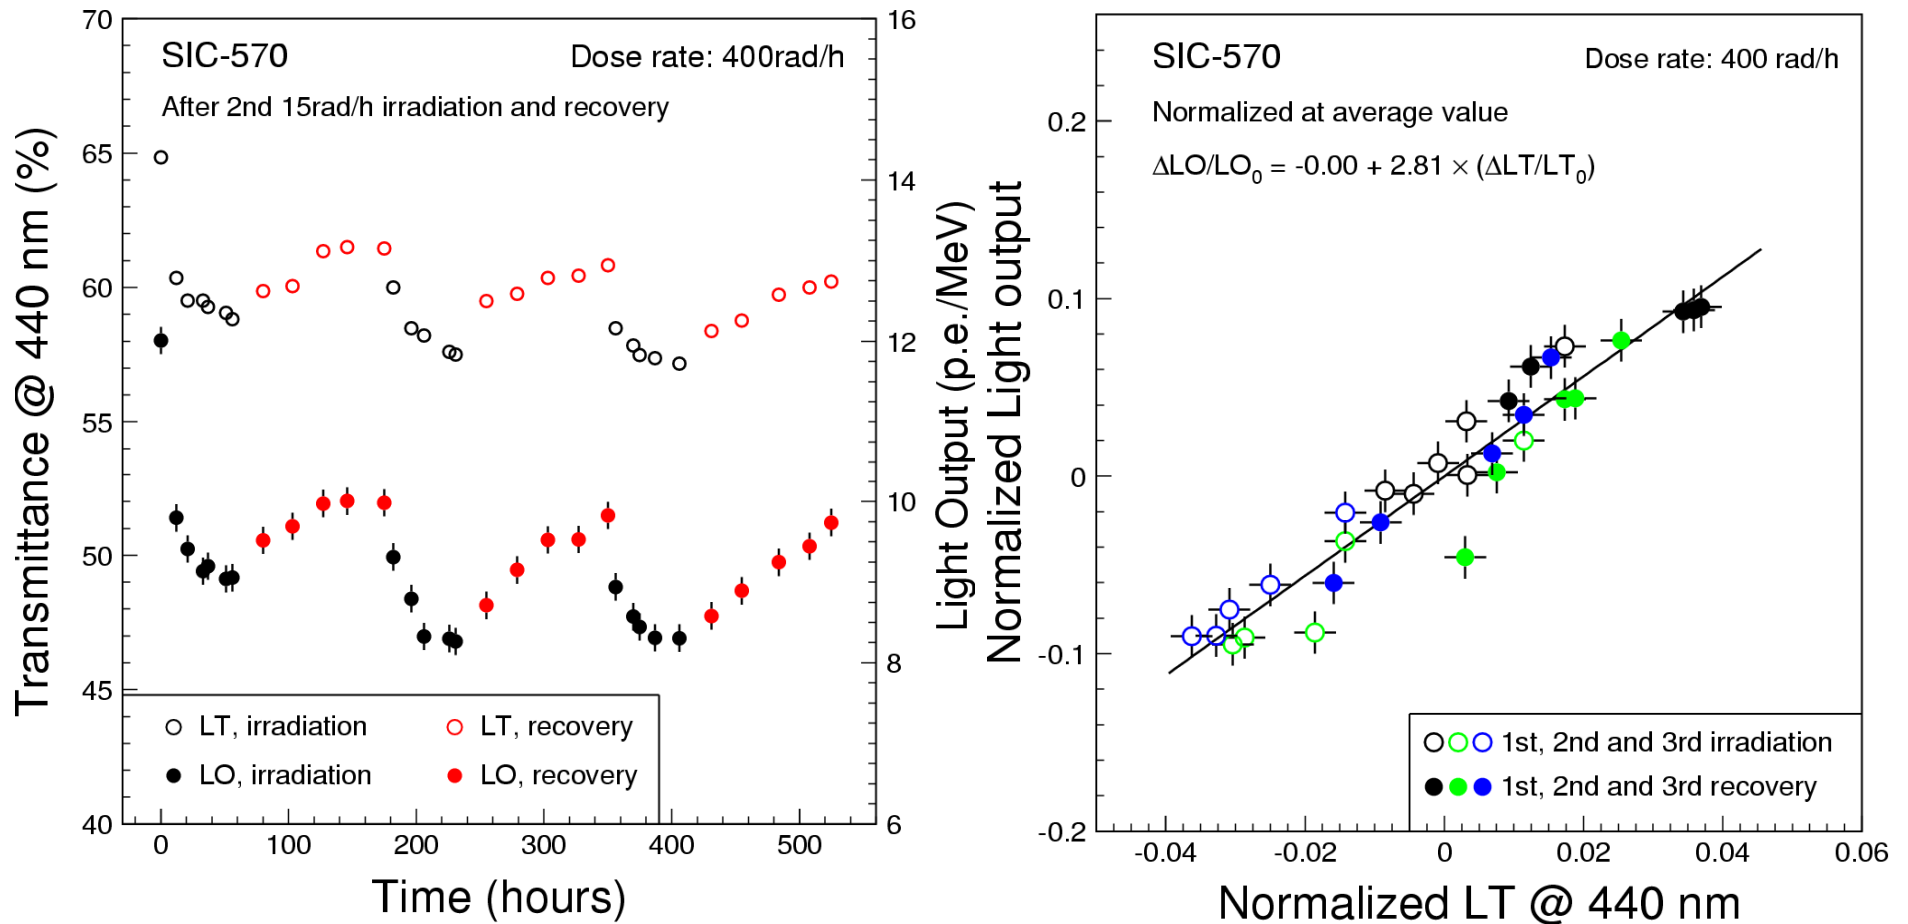




Radiation Induced Phosphorescence



Phosphorescence peaked at 430 nm
with decay time constant of 2.5 h observed

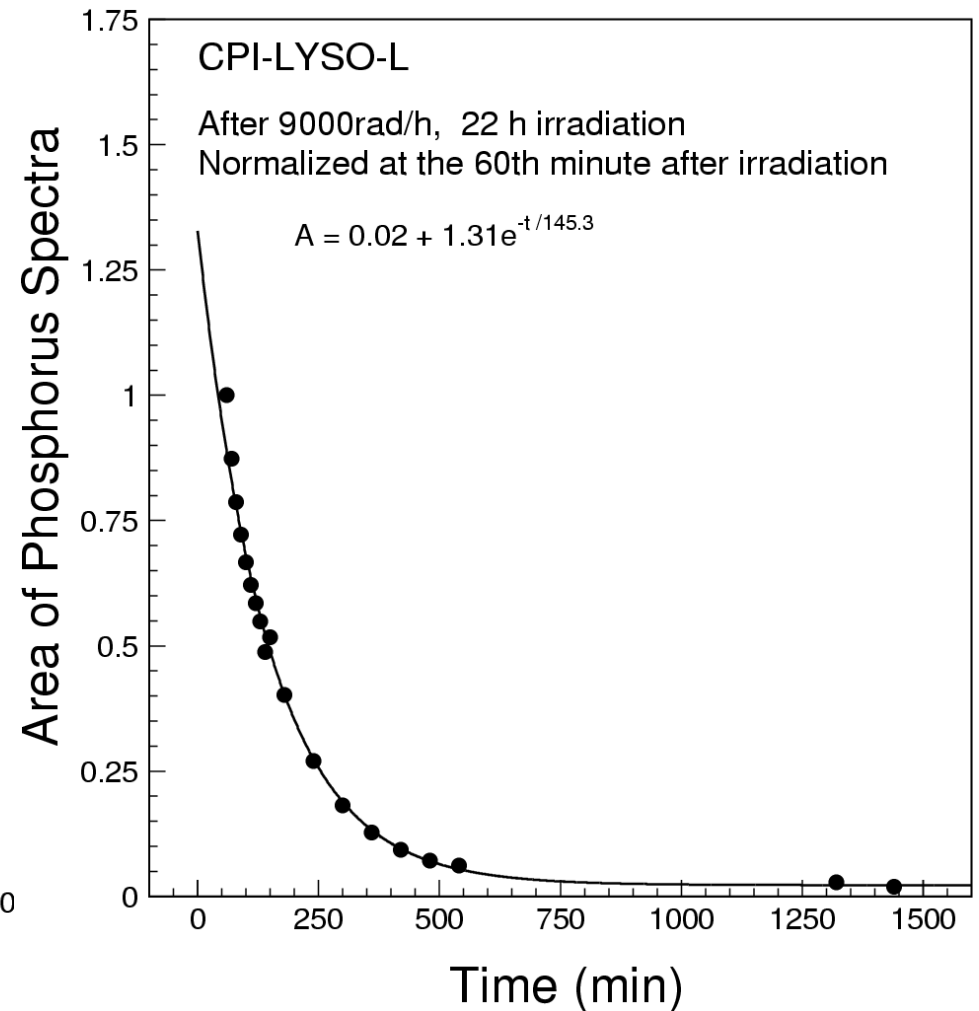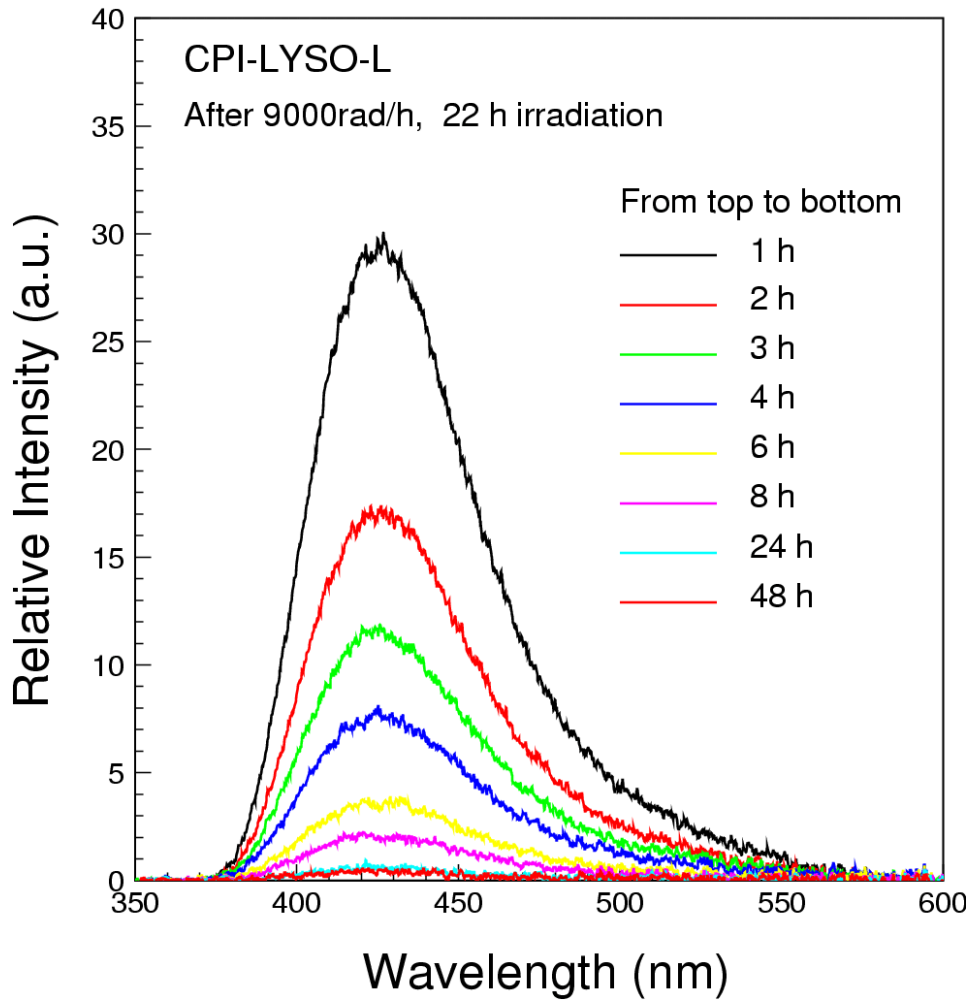




γ -ray Induced Readout Noise



Sample ID	L.Y. p.e./MeV	F μ A/rad/h	$Q_{15 \text{ rad/h}}$ p.e.	$Q_{500 \text{ rad/h}}$ p.e.	$\sigma_{15 \text{ rad/h}}$ MeV	$\sigma_{500 \text{ rad/h}}$ MeV
CPI	1,480	41	6.98×10^4	2.33×10^6	0.18	1.03
SG	1,580	42	7.15×10^4	2.38×10^6	0.17	0.97

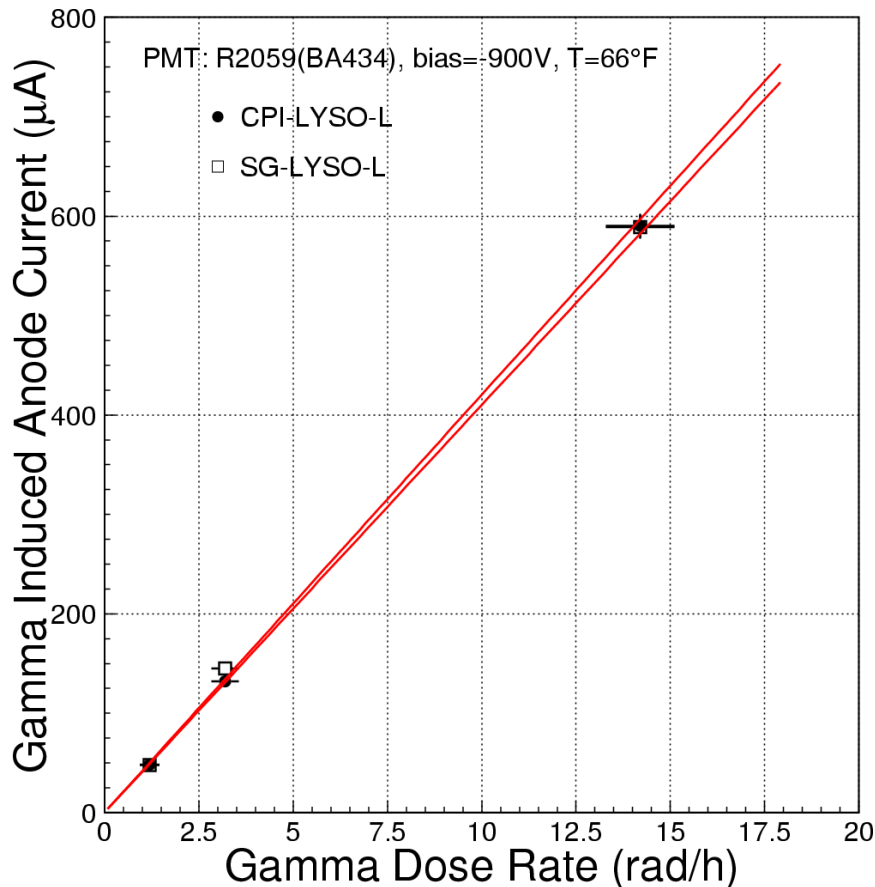

γ -ray induced PMT anode current can be converted to the photoelectron numbers (Q) integrated in 100 ns gate. Its statistical fluctuation contributes to the readout noise (σ).